



Standard Test Method for Moisture Retention Curves of Porous Building Materials Using Pressure Plates¹

This standard is issued under the fixed designation C 1699; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method specifies a laboratory procedure for the determination of the water retention curve (or moisture storage capacity) of porous building materials at very high relative humidity (RH) levels (\approx 95 to 100% RH) corresponding to the capillary moisture region of the sorption isotherm. This is achieved by using the pressure plate test apparatus. This technique was originally developed to study soil moisture content and eventually had been adapted to building construction materials.

1.2 At higher RH levels (\approx 95 to 100% RH) of the sorption isotherm (see Test Method C 1498), use of climatic chamber is not an option. This technique uses overpressure to extract water out of the pore structure of porous materials until equilibrium between the moisture content in the specimens and the corresponding overpressure is achieved. Using the pressure plate extractors, equilibrium can only be reached by desorption.

1.3 The values stated in SI units are to be regarded as standard. No other units of measurement are included in this standard.

1.4 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 *ASTM Standards:*²

C 1498 Test Method for Hygroscopic Sorption Isotherms of Building Materials

D 2325 Test Method for Capillary-Moisture Relationships for Coarse- and Medium-Textured Soils by Porous-Plate Apparatus³

D 3152 Test Method for Capillary-Moisture Relationships for Fine-Textured Soils by Pressure-Membrane Apparatus³

E 337 Test Method for Measuring Humidity with a Psychrometer (the Measurement of Wet- and Dry-Bulb Temperatures)

3. Terminology

3.1 *Definitions of Terms Specific to this Standard:*

3.1.1 *desorption isotherm*—the sorption isotherm measured exclusively during the hygroscopic desorption process started from the condition of full water saturation of the material.

3.1.2 *sorption isotherm*—relationship between the relative humidity (see Test Method E 337) and the equilibrium moisture content of the material, at a specified temperature.

3.1.3 *pressure-plate facility*—Heavy steel vessel capable of holding different pressure levels.

3.1.4 *moisture content, by mass*—mass of water retained in the specimen divided by the dry mass of the specimen.

4. Significance and Use

4.1 The purpose of this test is to obtain, by means of a specified laboratory procedure, the values of the equilibrium moisture content at higher RH levels (\approx 95 to 100%). These values are used either as means to characterize the material or as material characteristics needed as input to appropriate computer models that can simulate wetting or drying potential of individual building materials or material assemblies under specified environmental conditions.

5. Apparatus

5.1 *Pressure vessel*—Heavy-duty steel vessels of approximately 305 mm in diameter and about 75 mm or 250 mm high with heavy top lid tightly-held against O-ring gasket by clamping bolts (see Fig. 1).


5.2 *Porous ceramic plates*—This is the plate upon which the specimens sit and is composed of microscopic pores allowing

¹ This test method is under the jurisdiction of ASTM Committee C16 on Thermal Insulation and is the direct responsibility of Subcommittee C16.33 on Insulation Finishes and Moisture.

Current edition approved Oct. 15, 2008. Published November 2008.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

³ Withdrawn. The last approved version of this historical standard is referenced on www.astm.org.

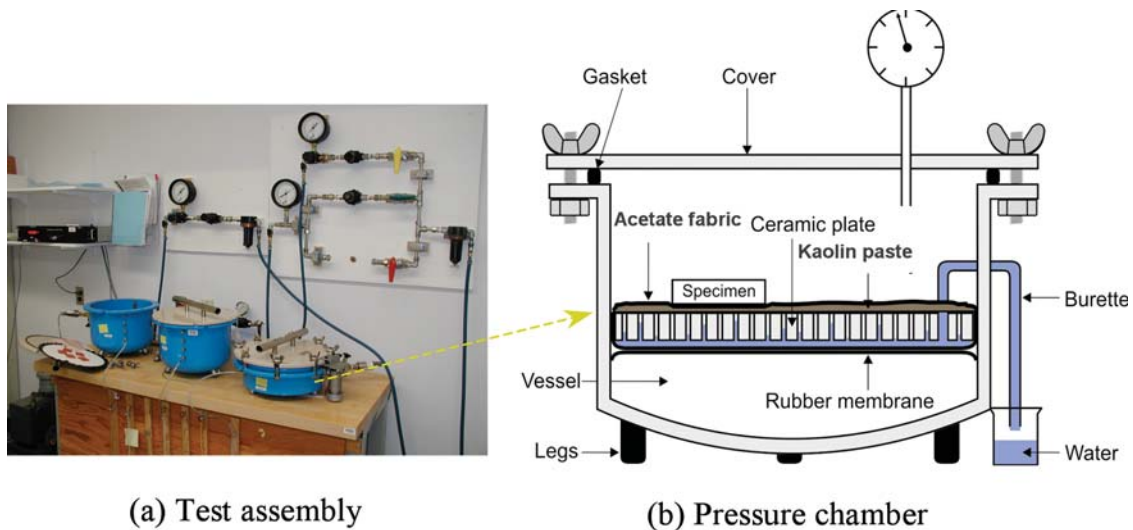

(a) Test assembly

(b) Pressure chamber

FIG. 1 Pressure Plate Test Apparatus

only water to flow through it. The plate assembly is exposed to an overpressure that can be adjusted, while the other side of the plate is always at atmospheric pressure resulting in a pressure difference over the plate and the specimens.

5.3 *Balance*—An analytical balance capable of weighing within 1 mg shall be used. The accuracy of the balance shall be at least ± 0.1 percent of the total specimen weight.

5.4 *Drying oven*—A ventilated drying oven, capable of maintaining the required drying temperature within $\pm 2K$ for temperatures less than $75^\circ C$ and $\pm 4K$ for temperatures above $75^\circ C$, and a relative humidity of less than 10%, shall be used. In warm-humid laboratory environment or at low drying temperatures, it will be necessary to provide a supply of dried air to achieve the less than 10 % relative humidity specification in the drying oven.

5.5 *Desiccator equipped with outflow knob*—Used as a vacuum chamber to remove air (that is, evacuate) from the water and evacuate specimens.

5.6 *Kaolin paste and acetate fabric*—This clay paste ensures good hydraulic contact between plate/specimen. The acetate fabric prevents contamination of the specimens by the clay.

5.7 *Pressure source*—Compressed air or nitrogen in cylinders, or high-pressure air compressor.

5.8 *Pressure manifold*—Assembly of conduits and valves regulating the air supplied to the extractors.

6. Test Specimens

6.1 A test specimen shall be cut to approximately 15 cm² and have a thickness as minimal as possible (≈ 5 mm, depending on the structure of the material) to reduce the time to reach equilibrium.

6.2 A minimum of five specimens shall be tested in each pressure environment. The test procedure, as specified below, and the precision of weighing shall be applied to each specimen.

7. Preparations of Test Specimens

7.1 Dry specimens in oven to constant weight (see Note 1).

7.2 Measure and record dry specimen dimensions.

7.3 For vacuum saturation (see Note 2), follow steps 7.3.1 to 7.3.3

7.3.1 Place them in a vacuum chamber (that is, desiccator equipped with outflow knob and connected to vacuum pump) and evacuate for 24 hours. This ensures that no air remains in the pores when specimens are being saturated.

7.3.2 Evacuate distilled water by pumping air out for 1 to 2 hours.

7.3.3 Use this water to saturate the specimens under vacuum. The assembly remains under vacuum for at least 3 days or until no air bubbles are observed. Keep the specimens fully submerged in the vacuum chamber until ready for measurement. This minimizes the amount of drying that can occur.

7.4 For capillary saturation (see Note 3), specimens shall be immersed completely in distilled water (kept at room temperature) until a constant weight is attained.

7.5 Soak the porous ceramic plate(s) in distilled water for a minimum of 8 hours.

7.6 Prepare the kaolin paste by mixing 125g of kaolin powder with 150g water and apply it directly onto the saturated plate.

7.7 Cover the paste with a layer of acetate cloth to prevent the kaolin from sticking to the specimens.

7.8 Remove excess water off specimen surfaces by patting on a damp sponge and record specimen masses.

7.9 Press each specimen firmly on the acetate cloth ensuring good contact and also removal of any air bubbles underneath.

7.10 Close the pressure plate extractor lid after ensuring good connection of the outflow tube to the ceramic plate.

NOTE 1—typically, the following temperatures are used for drying the test specimens: (a) for materials which do not change either structure or dimensions at $105^\circ C$, ($221^\circ F$), for example, some mineral materials, use $105 \pm 4^\circ C$ ($221 \pm 8^\circ F$), (b) for materials, in which structural or dimensional changes occur between $70^\circ C$ ($158^\circ F$) and $105^\circ C$ ($221^\circ F$), for example, some cellular plastics, use $70 \pm 2^\circ C$ ($158 \pm 4^\circ F$), (c) for materials, in which elevated temperatures bring about chemical or physical changes, for example, crystalline water in gypsum or blowing agent solubility in some cellular plastics, use $40 \pm 2^\circ C$ ($104 \pm 4^\circ F$), and (d) when drying at the specified aforementioned temperatures adversely

affects the building material, dry specimen to moisture free weight (that is dry weight, see 7.1) in a desiccator at room temperature or inside an airtight chamber flushed with dry air having a dew point less than [ape] – 40°C.

NOTE 2—Vacuum saturation leads to the maximum possible equilibrium moisture content in a material and is relevant to underwater and below-grade construction.

NOTE 3—Capillary saturation is relevant to above-grade construction.

8. Procedure

8.1 The room temperature shall remain constant at 22 ± 1°C (73° ± 2°F) for the duration of the test. If the lid or the body of the extractor cools down then condensation will occur inside the pressure vessel and it will give erroneous results.

8.2 Check the initial pressure transducer voltage reading and make adjustment, if necessary.

8.3 Connect the external outflow tube to a flexible plastic tube and place it into a burette’s opening so it can be noted when moisture equilibrium is obtained.

8.4 Open air-control valves to admit compressed air or gas. Adjust the pressure regulator (see Note 4) until the desired pressure is reached in order to extract moisture from specimens. Record the pressure.

8.5 Bring test specimens to equilibrium state of moisture content, first at one of the lower suction pressure, given in Table 1, and consecutively at other user-determined pressure levels. Equilibrium is achieved when the water outflow (in the burette) is less than 0.05mL in 48 hours (see Note 5).

8.6 Clamp off flexible plastic tube. Release the air pressure from the pressure plate extractor, open the lid and remove specimens to immediately determine their masses gravimetrically.

8.7 Rewet Kaolin paste with excess of distilled water. Place specimens back on a ceramic plate and repeat from step 8.3 until all user-determined suction pressures are covered. Depending on the pressure ranges, a combination of several different pressure plates/extractors will be required. When moving from one extractor to another, a new saturated ceramic plate is used along with fresh clay paste. Above 15 bar pressure, the use of higher-pressure systems with cellulose membranes instead of ceramic plates is necessary.

8.8 After all pressure plate measurements are completed, place specimens in oven and dry to constant weight. This final dry mass (m₀) is used to calculate moisture contents.

NOTE 4— It is important to manage the regulator so that the desired pressure is approached from a lower pressure. That is, do not overpressure the chamber and then reduce the pressure to the desired level.

NOTE 5—Depending on the nature of the material, this can take several days, weeks and even months.

9. Calculation

9.1 Calculate the moisture content, u (kg·kg⁻¹), for each specimen at each suction pressure (that is, gauge pressure) as follows:

$$u = \frac{(m_0 - m_0)}{m_0} \tag{1}$$

m = the mass of the specimen at equilibrium, and
m₀ = that of the dry specimen.

9.2 Calculate the average moisture content, U (kg·kg⁻¹), of specimens at each suction pressure levels.

9.3 The relative humidity (RH) can be calculated either from Eq 2 or obtained from Table 1. The equilibrium suction pressure (P_h) can be converted to the RH (φ) using:

$$\ln\phi = -\frac{M}{\rho RT} P_h \tag{2}$$

M = the molar mass of water

R = he ideal gas constant

T = the thermodynamic temperature and

ρ = the density of water

10. Report

10.1 The test report shall include the following:

10.1.1 Reference to this ASTM Standard.

10.1.2 *Product identification:*

10.1.2.1 Name, manufacturer or supplier,

10.1.2.2 Type, as in manufacturer’s specification,

10.1.2.3 Production code number, if any,

10.1.2.4 Packaging,

10.1.2.5 The form in which it arrived at the laboratory,

10.1.2.6 Nominal physical characteristics; for example, bulk density, thickness, etc.,

10.1.3 *Test procedure with:*

10.1.3.1 Factors if any, which have had the potential to influence the results,

10.1.3.2 Date of test, and

10.1.3.3 Drying temperature, relative humidity and drying procedure

10.1.4 *Results:*

10.1.4.1 Table of measured pressures, equivalent RH and moisture content, temperature and

10.1.4.2 Graph showing the RH vs. moisture content (U) plot.

11. Precision and Bias

11.1 The reproducibility and precision of this test method is yet to be established.

12. Keywords

12.1 moisture content; pressure plate apparatus; water vapor sorption

TABLE 1 Suction Pressure Set-Points and Corresponding Relative Humidity

Suction Pressure PA	Equivalent Pressure bar	RH %
50000	0.50	99.96
75000	0.75	99.94
100000	1.0	99.93
350000	3.5	99.74
500000	5.0	99.63
750000	7.5	99.45
1000000	10.0	99.27
1500000	15.0	98.90
3000000	30.0	97.81

BIBLIOGRAPHY

- (1) Nordtest Method: NT BUILD 481, Building Materials: Retention Curve and Pore Size Distribution. November, (Toronto, Ontario, April 01, 2006), pp. 1-9, November 01, 2006 (Also published in Symposium on Heat, Air and Moisture Transport Properties of Building Materials, ASTM, Toronto, Ontario, April 2006, pp. 1-18.) doi:10.1520/JAI100265, (NRCC-48382)URL: <http://irc.nrc-cnrc.gc.ca/pubs/fulltext/nrcc48382/>
- (2) Kumaran, M.K.; Mukhopadhyaya, P.; Normandin, N. "Determination of equilibrium moisture contents of building materials: some practical difficulties," Journal of ASTM International, 3, (10),

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).