



Standard Specification for Porous Concrete Pipe (Metric)¹

This standard is issued under the fixed designation C 654M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last approval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

This standard has been approved for use by agencies of the Department of Defense.

1. Scope

1.1 This specification covers porous nonreinforced concrete pipe for use in underdrains.

1.2 This specification is the metric counterpart of Specification C 654.

2. Referenced Documents

2.1 *ASTM Standards*:²

C 33 Specification for Concrete Aggregates

C 150 Specification for Portland Cement

C 497M Test Methods for Concrete Pipe, Manhole Sections, or Tile [Metric]

C 595 Specification for Blended Hydraulic Cements

C 618 Specification for Coal Fly Ash and Raw or Calcined Natural Pozzolan for Use in Concrete

C 822 Terminology Relating to Concrete Pipe and Related Products

C 989 Specification for Ground Granulated Blast-Furnace Slag for Use in Concrete and Mortars

C 1116 Specification for Fiber-Reinforced Concrete and Shotcrete

3. Terminology

3.1 *Definitions*—For definitions of terms relating to concrete pipe, see Terminology C 822.

4. Classification

4.1 Pipe manufactured according to this specification shall be of two classes identified as “Standard-Strength Porous Nonreinforced Concrete Pipe” and “Extra-Strength Porous Nonreinforced Concrete Pipe.”

5. Basis of Acceptance

5.1 The acceptability of the pipe shall be determined by the results of the strength and porosity or rate of infiltration tests, and by inspection to determine whether the pipe conforms to this specification as to design and freedom from defects.

5.2 The pipe shall be acceptable under the strength tests when they have met the requirements as prescribed in Section 10.

5.3 *Acceptance as to Infiltration Properties*—Pipe shall be acceptable under the infiltration test when all test pipe conform to the test requirements as prescribed in Section 10.

6. Materials

6.1 *Concrete*—The concrete shall consist of cementitious materials, mineral aggregates, and water.

6.2 *Cementitious Materials*:

6.2.1 *Cement*—Cement shall conform to the requirements for portland cement of Specification C 150 or shall be portland blast-furnace slag cement, or slag-modified portland cement, or portland-pozzolan cement conforming to the requirements of Specification C 595, except that the pozzolan constituent in the Type IP portland-pozzolan cement shall be fly ash.

6.2.2 *Fly Ash*—Fly ash shall conform to the requirements of Specification C 618, Class F or Class C.

6.2.3 *Ground Granulated Blast Furnace Slag (GGBFS)*—GGBFS shall conform to the requirements of Grade 100 or 120 of Specification C 989.

6.2.4 *Allowable Combinations of Cementitious Materials*—The combination of cementitious materials used in the concrete shall be one of the following:

6.2.4.1 Portland cement only,

6.2.4.2 Portland blast furnace slag cement only,

6.2.4.3 Slag modified portland cement only,

6.2.4.4 Portland pozzolan cement only,

6.2.4.5 A combination of portland cement and fly ash,

6.2.4.6 A combination of portland cement and ground granulated blast-furnace slag, or

¹ This specification is under the jurisdiction of ASTM Committee C13 on Concrete Pipe and is the direct responsibility of Subcommittee C13.01 on Non-Reinforced Concrete Sewer, Drain and Irrigation Pipe.

Current edition approved Dec. 1, 2005. Published January 2006. Originally approved in 1980. Last previous edition approved in 2005 as C 654M – 05.

² For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

6.2.4.7 A combination of portland cement, fly ash (not to exceed 25 % of the total cementitious weight) and ground granulated blast furnace slag (not to exceed 25 % of the total cementitious weight).

6.3 *Aggregates*—Aggregates shall conform to Specification **C 33** except that the requirement for gradation shall not apply.

6.4 *Admixtures and Blends*—Admixtures and blends shall only be used with the approval of the owner.

6.5 *Synthetic Fibers*—Collated fibrillated virgin polypropylene fibers are not prohibited in concrete pipe as a nonstructural manufacturing material. Only Type III synthetic fibers designed and manufactured specifically for use in concrete and conforming to the requirements of Specification **C 1116** shall be accepted.

7. Design

7.1 *Design Tables*—Design requirements shall be in accordance with **Table 1** and **Table 2** and **Fig. 1**. Wall thickness used shall be not less than the value shown, except as affected by the tolerance herein specified.

8. Joints

8.1 The joints shall be of such design and the ends of the concrete pipe sections so formed that the pipe can be laid together to make a continuous line of pipe compatible with the permissible variations given in Section 7.

9. Manufacture

9.1 *Mixture*—The aggregates shall be sized, graded, proportioned, and mixed with such proportions of cementitious materials and water as will produce a homogeneous concrete mixture of such quality that the pipe will conform to the test and design requirements of this specification.

9.2 *Curing*—Pipe shall be subjected to any one of the methods of curing described in 9.2.1 through 9.2.3, or to any other method or combination of methods approved by the owner that will give satisfactory results. The pipe shall be cured for a sufficient length of time so that the concrete will develop the specified strength requirement at 28 days or less.

9.2.1 *Steam Curing*—Pipe shall be placed in a curing chamber, free from outside drafts, and cured in a moist

TABLE 1 Physical and Dimensional Requirements of Porous Concrete Pipe

Internal Designated Diameter, <i>D</i>	Minimum ^A Wall Thickness, <i>T</i>	Minimum Laying Length ^A	Minimum Socket Depth, <i>L_s</i>	Minimum Strength Three-Edge-Bearing	Minimum Infiltration
mm	mm	mm	mm	kN/m	L/s·m
100	25	600	25	14.5	0.8
150	25	600	25	16.0	1.0
200	32	600	32	19.0	1.5
250	35	600	35	20.5	2.0
300	38	600	38	22.0	2.5
375	44	600	44	25.5	3.0
450	50	600	50	29.0	3.5
525	57	600	57	32.0	4.0
600	63	600	63	35.0	4.5

^A Normally the minimum laying length is 600 mm in length, but if the owner has no objections, then 450-mm length pipe up to 300 mm in diameter shall be acceptable.

TABLE 2 Physical and Dimensional Requirements of Extra-Strength Porous Concrete Pipe

Internal Designated Diameter, <i>D</i>	Minimum ^A Wall Thickness, <i>T</i>	Minimum Laying Length ^A	Minimum Socket Depth, <i>L_s</i>	Minimum Strength Three-Edge-Bearing	Minimum Infiltration
mm	mm	mm	mm	kN/m	L/s·m
150	32	600	32	32.0	1.0
200	38	600	38	38.0	1.5
250	41	600	41	41.0	2.0
300	50	600	50	44.0	2.5
375	57	600	57	46.5	3.0
450	63	600	63	46.5	3.5

^A Normally the minimum laying length is 600 mm in length, but if the owner has no objections, then 450-mm length pipe up to 300 mm in diameter shall be acceptable.

TABLE 3 Permissible Variations in Dimensions of Porous Concrete Pipe

Internal Designated Diameter,	Limits of Permissible Variation			
	Wall Thickness, ^A	Length, Two Opposite Sides	Length,	Depth of Socket, ^A
mm	mm	mm	mm/m	mm
100	-2	6	-20	-3
150	-2	6	-20	-3
200	-2	8	-20	-6
250	-2	10	-20	-6
300	-2	10	-20	-6
375	-2	11	-20	-6
450	-2	13	-20	-6
525	-3	14	-20	-6
600	-3	14	-31	-6

^A The minus sign (-) indicates that the plus variation is not limited.

atmosphere maintained by the injection of steam for such time and at such temperature as needed to enable the pipe to meet the strength requirements. The curing chamber shall be constructed as to allow full circulation of steam around the entire pipe.


9.2.2 *Water Curing*—Concrete pipe shall be water-cured by covering with water-saturated material or by a system of perforated pipes, mechanical sprinklers, porous hose, or by any other approved method that will keep the pipe moist during the specified curing period.

9.2.3 The manufacturer has the option to combine the methods described in 9.2.1 and 9.2.2 provided the specified strength is attained.

9.3 *Specials*:

9.3.1 *General Requirements*—Special shapes or fittings such as wyes, tees, bends, and adapters for use with concrete pipe conforming to this specification shall be made of porous or nonporous concrete in such manner as will provide strength at least equal to the class of the adjacent pipe to which they are joined; and shall conform to all other requirements specified for pipe of corresponding class and internal diameter, except minimum infiltration. Joints shall be the same type as used in the adjoining pipe.

9.3.2 *Wyes and Tees*—Fabricated branches for wyes and tees shall be securely attached to the wall of the pipe and shall be flush with the inside surface of the pipe.

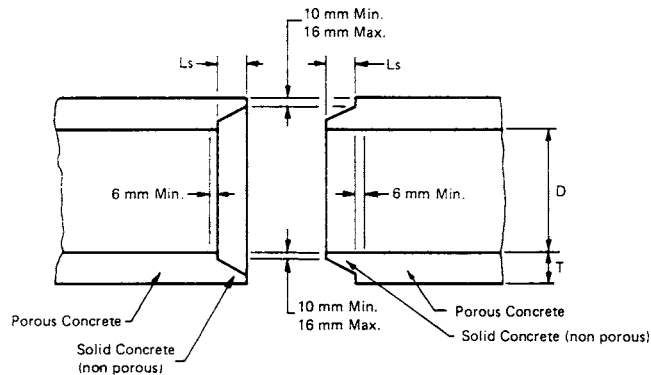

NOTE—See Tables 1 and 2 for values of *D*, *T*, and *L_s*.

FIG. 1 Joint Dimensions

10. Physical Requirements

10.1 *Test Specimen*—The specified number of pipe required for the tests shall be furnished by the manufacturer and shall be selected at random by the owner, and shall be pipe that would not otherwise be rejected under this specification. The selection shall be made at the point or points designated by the owner when placing the order. The test pipe shall first be freed from all visible moisture. When dry, each pipe shall be measured and inspected. The results of these observations shall be recorded.

10.2 *Number and Type of Test Specimens*—The manufacturer shall furnish pipe for crushing tests, up to 0.5 % of the number of pipe of each size included in the order, except that in no case shall less than two pipes be furnished.

10.3 *External Load Crushing Requirements*—The crushing strength of porous nonreinforced concrete pipe shall conform to the requirements prescribed in Table 1 and Table 2. The individual results of the various tests for each size of pipe and for each shipment and plant shall be tabulated separately. The crushing strength shall ordinarily be applied to not less than 75 % of the pipe received for purpose of test. All tests shall be made in accordance with Test Methods C 497M. Pipe shall be acceptable when all test pipe conform to the specified strength requirement. Should any of the test pipe provided in 10.2 fail to meet the strength requirement, the manufacturer will be allowed to test two pipe for each pipe that failed, and the pipe shall be acceptable only when all of these additional test pipe meet the strength requirement.

10.4 *Infiltration Requirement*—Infiltration (or porosity) shall conform to the requirements in Table 1 or Table 2.

10.4.1 The test pipe shall be placed with a spigot end down on a soft rubber nonpermeable mat, or its equivalent, and weighted or clamped down if necessary to prevent the escape of water through the spigot end of the pipe.

10.4.2 Water shall be introduced into the pipe, and the distance above the bottom of the porous section at which the water level becomes constant shall be determined. The rate of flow shall be at least equal to the required minimum infiltration for 1 m of pipe as given in Table 1 or Table 2.

10.4.3 The rate of infiltration per metre of pipe shall be determined as follows:

$$LITRES/s = L/h \tag{1}$$

where:

- LITRES/s* = infiltration rate in litres per second per metre of pipe,
- L* = litres per second of flow introduced into the test pipe, and
- h* = height in metres from the bottom of the porous section of the pipe at which the level of water becomes constant.

10.5 *Test Equipment*—The manufacturer shall furnish all equipment, facilities, and personnel necessary to perform at his plant the tests specified in Section 10. In the event that the owner elects to have tests performed at any other location, the manufacturer will not be required to furnish equipment, facilities, nor personnel.

11. Permissible Variations

11.1 Permissible variations from the dimensions described in Table 1 and Table 2 shall not exceed those stated in Table 3 and 11.2. This is not to be construed, however, that heavier wall thickness pipe cannot be furnished at the option of the manufacturer. Pipe intended to be straight shall not have variation in alignment of more than 10 mm/m of length.

11.2 *Internal Diameter*—See Table 4. At the manufacturer’s option, the internal diameter shall be one of two alternatives, the Designated Diameter or the Converted English Diameter. Pipe sections that are intended to be jointed to each other shall

TABLE 4 Internal Diameters

Designated Diameter, mm	Equivalent English Diameter, in.	Converted English Diameter, mm
100	4	102
150	6	152
200	8	203
250	10	254
300	12	305
375	15	381
450	18	457
525	21	533
600	24	610

be furnished with the same internal diameter alternative. The internal diameter of pipe manufactured to the Designated Diameters shall vary not more than ± 3 mm from the Designated Diameter for 100 mm and 150 mm and ± 6 mm for larger pipe. The internal diameter of pipe manufactured to the Converted English Diameters shall vary not more than ± 3 mm from the Converted English Diameter for 102 mm and 152 mm and ± 6 mm for larger pipe. For pipe manufactured to Converted English Diameters, the corresponding Designated Diameter shown in **Table 4** shall apply for all other requirements of this specification.

12. Repairs

12.1 Pipe repaired because of imperfections in manufacture or damage during handling will be acceptable, if in the opinion of the owner, the repaired pipe conforms to the requirements of this specification.

13. Inspection

13.1 The quality of all materials, the process of manufacture, and the finished pipe shall be subject to the inspection and approval by the owner. Such inspection shall be performed either at the point of manufacture or delivery.

14. Rejection

14.1 Pipe shall be subject to rejection on account of failure to conform to any of the specification requirements. It is not

prohibited for individual sections of pipe to be rejected because of any of the following:

14.1.1 Fractures or cracks passing through the wall or joints, except that a single crack not exceeding 50 mm in length at either end of a pipe or a single fracture in the joints not exceeding 75 mm in width nor more than 50 mm in length shall not be considered cause for rejection unless these defects exist in more than 5 % of the entire shipment or delivery.

14.1.2 The planes of the ends of the pipe are not perpendicular to the longitudinal axis, subject to the limits of variation as shown in **Table 3**.

14.1.3 Defects that indicate mixing and molding not in accordance with **9.1**.

14.1.4 Cracks sufficient to impair the strength, durability, or serviceability of the pipe.

15. Product Marking

15.1 The letters “ES” shall be legibly stamped with waterproof ink, or other permanent matter, on all extra-strength porous concrete pipe.

16. Keywords

16.1 concrete pipe; nonreinforced; porous; underdrains

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).