



Standard Test Method for Continuity of Coatings in Glassed Steel Equipment by Electrical Testing¹

This standard is issued under the fixed designation C 536; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method covers the detection of discontinuities in the glass coating of glassed steel equipment where such discontinuities would result in early failure due to the attack of the chemical contents of the vessel on the metal substrate. It is applicable to (1) provide a manufacturing and inspection test of glassed-steel equipment designed for relatively mild, low-temperature corrosive service, and (2) the field testing of similar equipment used in more severely corrosive environment.

NOTE 1—A manufacturing test method for the latter type of equipment is described in Method C 537.

1.2 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Document

2.1 ASTM Standards:

C 537 Test Method for Reliability of Glass Coatings on Glassed Steel Reaction Equipment by High Voltage²

3. Summary of Test Method

3.1 The test method consists essentially of grounding the metal structure of the equipment being tested to the ground side of a voltage generator and sweeping the surface of the glass with a suitable probe electrically connected to the other side of the generator. Wherever a discontinuity exists, a discharge will give a positive indication that such a discontinuity exists. The voltage is set at 5000 V in order to show existing discontinuities without breaking through the existing glass coating. A built-in current limiting device ensures electrical safety for the operator.

4. Significance and Use

4.1 This test method is designed to detect existing discontinuities in the glass coating of glassed steel equipment while

maintaining a voltage low enough as to be unlikely to cause breakdown of the coating. The test is adaptable for manufacturing inspection in the processing of equipment and for field use to find existing defects which can be “plugged” or repaired before serious damage is done to the equipment. As a means of positive detection, it is applicable to process studies, quality control, or specification.

5. Definition

5.1 *glassed steel (glass-lined steel or glass-coated steel)*—designations generally applied to a class of porcelain enamels that have high resistance to chemical attack at elevated temperatures and pressures.

6. Interferences

6.1 Since the test method is electrical, it is necessary to have a good ground connection between the instrument and the metal substrate of the equipment being tested. It is also necessary that the surfaces of the glass be reasonably clean and dry. A wet surface will conduct enough voltage to any exposed metal to give an indication of a “contact” over a large area instead of at a specific area of discontinuity. Such a capacitance discharge can be distinguished from a true failure by extending over a large area instead of at local spots that could be identified and marked for repair.

7. Apparatus³

7.1 The test apparatus comprises a voltage stabilizing transformer, a step-up transformer, a current-limiting resistance, a voltmeter and pilot light, along with a suitably insulated cable and probe handle equipped with interchangeable wire brush-type and point electrodes (see Fig. 1 for a schematic wiring diagram). The current output is limited to 2.5 mA. The wire brush-type electrode is designed for sweeping larger areas of glass coating while the point electrode is better adapted to corners and the more restricted areas.

7.2 A portable 5000-volt d-c tester may be used in this test method.

¹ This test method is under the jurisdiction of ASTM Committee B-8 on Metallic and Inorganic Coatings and is the direct responsibility of Subcommittee B08.12 on Materials for Porcelain Enamel and Ceramic-Metal Systems.

Current edition approved Feb. 25, 1983. Published April 1983. Originally published as C 536 – 64 T. Last previous edition C 536 – 77.

² *Annual Book of ASTM Standards*, Vol 02.05.

³ When requesting information, specific reference should be made to the ASTM Designation number. Suitable test equipment is available from: Associated Research, Inc., 3758 West Belmont Ave., Chicago, IL 60618 or The Pfadler Co., A Div. of Sybron Corp., 1000 West Ave., Rochester, NY 14603.

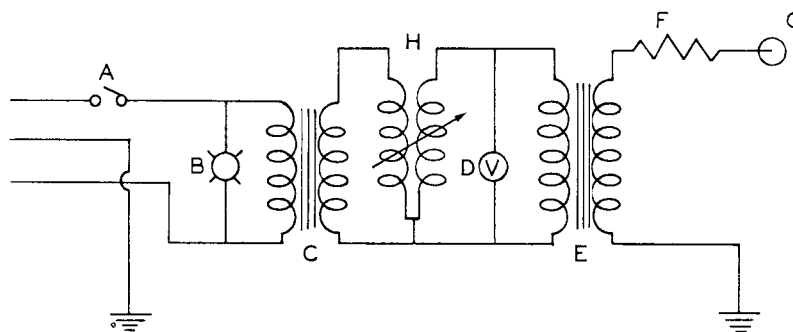


FIG. 1 Circuit Diagram, 5000 V A-C Tester

8. Safety Precautions

8.1 The equipment being tested should be well grounded as well as electrically connected to the ground side of the testing apparatus.

8.2 The probe should be handled only by the insulating plastic handle.

8.3 Keep the probe electrode away from personnel and from conducting surfaces that might lead to personnel.

8.4 Turn the switch off and ground the electrode before changing probe heads. Although the current is low enough to be electrically safe, the involuntary reaction to a surprise discharge can cause injury.

9. Procedure

9.1 Using a 14-gage (1.63-mm) (or heavier) wire, connect the ground connection of the tester to the cleaned metal substrate of the equipment to be tested. A similar connection should be made to a suitable external ground.

9.2 Attach the probe cable to the tester and the desired probe electrode to the end of the probe handle.

9.3 Connect the input to a 115 to 120-V, 60-Hz source, or use a portable 5000-volt d-c unit.⁴

⁴ Suitable test equipment is available from: The Pfadler Co., 1000 West Avenue, Rochester, NY 14603; Edlon Plastics, 6 Pheasant Run, Newton, Pa 18940; Buckley's (Uvral) Ltd., Beta Works, Range Road, Hythe, Kent CT21 6HG, England, United Kingdom.

9.4 While holding the probe by the plastic handle move the switch to the on position. A red pilot light indicates that the tester is in operation.

9.5 Apply the test probe lightly to the surface of the glass coating in a sweeping motion to cover the whole area to be tested. If the interferences are not too great, a spark should also be seen and heard as it arcs between the electrode and the metal substrate.

9.6 Mark each area where a contact is found using suitably colored chalk or crayon.

9.7 Turn the switch off and ground the electrode to the metal ground before laying the probe down or changing the electrodes on the probe.

10. Report

10.1 The report shall include the following:

10.1.1 Date of test,

10.1.2 Description or identification of equipment being tested, and

10.1.3 Number and location of failures.

11. Precision and Bias

11.1 No justifiable statements can be made regarding the precision and bias of this test method because it is designed for application to full-size production vessels and reactors with the result that variables due to design, metal composition, fabrication, and metal processing, as well as porcelain enameling, are introduced into the results.

The American Society for Testing and Materials takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).