



Standard Specification for Contact-Molded Reinforced Thermosetting Plastic (RTP) Laminates for Corrosion-Resistant Equipment¹

This standard is issued under the fixed designation C 582; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This specification covers composition, thickness, fabricating procedures, and physical property requirements for glass fiber reinforced thermoset polyester, vinyl ester, or other qualified thermosetting resin laminates comprising the materials of construction for RTP corrosion-resistant tanks, piping, and equipment. This specification is limited to fabrication by contact molding.

NOTE 1—The laminates covered by this specification are manufactured during fabrication of contact-molded RTP tanks, piping, and other equipment.

NOTE 2—There is no similar or equivalent ISO standard.

1.2 The following safety hazards caveat pertains only to the test method portion, Section 8, of this specification: *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety and health practices and determine the applicability of regulatory limitations prior to use.*

2. Referenced Documents

2.1 ASTM Standards:

- C 581 Practice for Determining Chemical Resistance of Thermosetting Resins Used in Glass Fiber Reinforced Structures Intended for Liquid Service²
- D 638 Test Method for Tensile Properties of Plastics³
- D 695 Test Method for Compressive Properties of Rigid Plastics³
- D 790 Test Methods for Flexural Properties of Unreinforced and Reinforced Plastics and Electrical Insulating Materials³
- D 883 Terminology Relating to Plastics³
- D 2583 Test Method for Indentation Hardness of Rigid Plastics by Means of a Barcol Impressor⁴

¹ This specification is under the jurisdiction of ASTM Committee D20 on Plastics and is the direct responsibility of Subcommittee D20.23 on Reinforced Plastic Piping Systems and Chemical Equipment.

Current edition approved Nov. 10, 2002. Published January 2003. Originally approved in 1965. Last previous edition approved in 1995 as C 582 – 95.

² Annual Book of ASTM Standards, Vol 08.04.

³ Annual Book of ASTM Standards, Vol 08.01.

⁴ Annual Book of ASTM Standards, Vol 08.02.

D 2584 Test Method for Ignition Loss of Cured Reinforced Resins⁴

D 3681 Test Method for Chemical Resistance of “Fiber-glass” (Glass-Fiber-Reinforced Thermosetting-Resin) Pipe in a Deflected Condition²

E 84 Test Method for Surface Burning Characteristics of Building Materials⁵

3. Definitions

3.1 Definitions used in this specification are in accordance with Terminology D 883 unless otherwise indicated. The abbreviation for reinforced thermoset plastic is RTP.

3.2 *polyester*—resins produced by the polycondensation of dihydroxyderivatives and dibasic organic acids or anhydrides, wherein at least one component contributes ethylenic unsaturation yielding resins that can be compounded with styryl monomers and reacted to give highly crosslinked thermoset copolymers.

3.3 *vinyl ester*—resins characterized by reactive unsaturation located predominately in terminal positions that can be compounded with styryl monomers and reacted to give highly crosslinked thermoset copolymers.

NOTE 3—These resins are handled in the same way as polyesters in fabrication of RTP components.

3.4 *contact molding*—a method of fabrication wherein the glass-fiber reinforcement is applied to the mold, in the form of chopped strand mat or woven roving, by hand or from a reel, or in the form of chopped strands of continuous-filament glass from a chopper-spray gun. The resin matrix is applied by various methods, including brush, roller, or spray gun. Consolidation of the composite laminate is by rolling.

4. Classification

4.1 Laminates shall be classified according to type, class, and grade.

4.1.1 *Type*—In Roman numerals, shall designate the reinforcement structure comprised of specific plies of glass fiber in specific sequences.

4.1.1.1 *Type I*—A standard all-mat or chopped-roving construction, or both, as shown in Table 1.

⁵ Annual Book of ASTM Standards, Vol 04.07.

TABLE 1 Standard Laminate Composition Type I^A

Calculated Thickness ^{BC}		Corrosion Barrier ^D		Structural Plies ^E															Drafting Symbols
		Number and Sequence of Plies																	
in.	(mm)	1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	
0.18	(4.6)	V	M	M	M	M													V, 4M
0.23	(5.8)	V	M	M	M	M	M												V, 5M
0.27	(6.9)	V	M	M	M	M	M	M											V, 6M
0.31	(7.9)	V	M	M	M	M	M	M	M										V, 7M
0.35	(8.9)	V	M	M	M	M	M	M	M	M									V, 8M
0.40	(10.2)	V	M	M	M	M	M	M	M	M	M								V, 9M
0.44	(11.2)	V	M	M	M	M	M	M	M	M	M	M							V, 10M
0.48	(12.2)	V	M	M	M	M	M	M	M	M	M	M	M						V, 11M
0.53	(13.5)	V	M	M	M	M	M	M	M	M	M	M	M	M					V, 12M
0.57	(14.5)	V	M	M	M	M	M	M	M	M	M	M	M	M	M				V, 13M
0.61	(15.5)	V	M	M	M	M	M	M	M	M	M	M	M	M	M	M			V, 14M
0.66	(16.8)	V	M	M	M	M	M	M	M	M	M	M	M	M	M	M	M		V, 15M
0.70	(17.8)	V	M	M	M	M	M	M	M	M	M	M	M	M	M	M	M	M	V, 16M
0.74	(18.8)	V	M	M	M	M	M	M	M	M	M	M	M	M	M	M	M	M	M

^A Glass content, weight, % = 25 to 30, all thickness.

^B Calculated thickness for design purposes is determined as follows:

V = Surfacing mat – 0.010 in./ply (0.25 mm/ply) when saturated with resin.

M = 1 1/2 oz/ft² (459 g/m²) mat – 0.043 in./ply (1.1 mm/ply) when saturated with resin.

^C The thickness shall be not less than 90 % of the calculated thickness shown.

^D Corrosion barrier (Plies 1, 2, and 3) shall gel before structural plies are added.

^E Structural lay-up may be interrupted at intervals long enough to exotherm if required by the laminate manufacturing procedure and 6.3.1.

4.1.1.2 *Type II*—A standard mat or chopped-roving and woven-roving construction, or combination thereof, as shown in Table 2.

4.1.1.3 Other types, such as standard mat or chopped roving with alternating layers of nonwoven biaxial or unidirectional reinforcement in the structured plies, may be qualified in accordance with Appendix X2.

4.1.2 *Class*—In capital letters, shall designate the generic resin: “P” for polyester and “V” for vinyl ester. The letters “FS” followed by parenthesis, “FS(),” shall designate fire retardancy, if specified, with maximum flame spread in the parentheses in accordance with Test Method E 84.

NOTE 4—Fire retardancy by Test Method E 84 is determined for 0.125-in. (3.175-mm) thick, flat laminates with all-mat glass content of 25 to 30 %.

NOTE 5—Maximum flame spread designation by Test Method E 84 relates to measurement and description of the properties of materials, products, or systems in response to heat and flame under controlled laboratory conditions and should not be considered or used for the description or appraisal of the fire hazard of materials, products, or systems under actual fire conditions. However, results of this test may be used as elements of a fire risk assessment that takes into account all the factors that are pertinent to an assessment of the fire hazard or a particular end use.

TABLE 2 Standard Laminate Composition Type II

Calculated Thickness ^{A,B}		Glass Content (weight, %)	Corrosion Barrier ^C		Structural Plies ^D																	Drafting Symbols		
in.	(mm)		Number and Sequence of Plies																					
			1	2	3	4	5	6	7	8	9	10	11	12	13	14	15	16	17	18	19	20	21	
0.22	(5.6)	28 to 33	V	M	M	M	R	M																V, 2M, MRM
0.29	(7.4)	30 to 35	V	M	M	M	R	M	R	M														V, 2M, 2(MR)M
0.37	(9.4)	30 to 35	V	M	M	M	R	M	R	M	R	M												V, 2M, 3(MR)M
0.41	(10.4)	30 to 35	V	M	M	M	R	M	R	M	R	M	M											V, 2M, 3(MR)M, M
0.49	(12.5)	34 to 38	V	M	M	M	R	M	R	M	R	M	M	R	M									V, 2M, 3(MR)M, MRM
0.57	(14.5)	34 to 38	V	M	M	M	R	M	R	M	R	M	M	R	M	R	M							V, 2M, 3(MR)M, 2(MR)M
0.64	(16.3)	37 to 41	V	M	M	M	R	M	R	M	R	M	M	R	M	R	M	R	M					V, 2M, 3(MR)M, 3(MR)M
0.69	(17.5)	37 to 41	V	M	M	M	R	M	R	M	R	M	M	R	M	R	M	R	M	M				V, 2M, 3(MR)M, 3(MR)M, M
0.76	(19.3)	37 to 41	V	M	M	M	R	M	R	M	R	M	M	R	M	R	M	R	M	M	R	M		V, 2M, 3(MR)M, 3(MR)M, MRM

^A Calculated thickness for design purposes is determined as follows:

V = Surfacing mat – 0.010 in./ply (0.25 mm/ply) when saturated with resin.

M = 1 1/2 oz/ft² (459 g/m²) mat = 0.043 in./ply (1.1 mm/ply) when saturated with resin.

R = 24 1/2 oz/yd² (832 g/m²) 5 × 4 woven roving = 0.033 in./ply (0.84 mm/ply) when saturated with resin.

^B The thickness shall be not less than 90 % of the calculated thickness shown.

^C Corrosion barrier (Plies 1, 2, and 3) shall gel before structural plies are added.

^D Structural lay-up may be interrupted long enough to exotherm following an “M” ply, if required by the laminate manufacturing procedure. Location of exotherm plies may be shifted within the laminate body. No plies may be omitted. Refer to 6.3.1.

4.1.3 *Grade*—In Arabic numerals, shall designate the minimum physical property levels of a laminate at $73.4 \pm 3.6^{\circ}\text{F}$ ($23 \pm 2^{\circ}\text{C}$).

NOTE 6—The five Arabic grade numbers designate minimum physical property levels of a laminate obtained from tests of representative production process samples. They are not arbitrarily selected values.

4.1.4 *Thickness*—Nominal, shall be designated by Arabic number in decimal hundredths of an inch. (See Table 1 and Table 2 for standard thicknesses.)

NOTE 7—Table 1 and Table 2 are for reference purposes and do not preclude other laminate-type constructions, such as nonwoven biaxial or unidirectional fabric, which may be agreed upon between the buyer and the seller, or may be added to this specification if they have been fully identified and characterized, as shown in Appendix X2.

4.1.5 *Classification Requirements for Different Laminates*—Laminate designation from Table 3 shall consist of the abbreviation RTP followed by (1) type in Roman numerals; (2) class in capital letters followed by FS() if required; (3) grade consisting of five Arabic numbers to designate minimum levels of physical properties and (4) thickness designated by Arabic number in decimal inches (or ALL, if properties apply to all thicknesses).

4.1.5.1 Examples:

(1) RTP I P 13211 ALL, designates Type I polyester laminate, non-fire-retardant Grade 13211, having the following minimum physical property levels (see Table 3):

Tensile strength, ultimate—9000 psi (62 MPa).

Tensile modulus—1 050 000 psi (7242 MPa).

Flexural strength, ultimate—18 000 psi (124 MPa).

Flexural modulus—700 000 psi (4828 MPa).

Glass content—25 %.

Thickness—“ALL” thicknesses.

(2) RTP II P FS(25) 55433.30, designates Type II, polyester fire-retardant resin laminate with a maximum flame spread of 25, Grade 55433 having the following minimum

physical property levels (see Table 3):

Tensile strength, ultimate—17 500 psi (121 MPa).

Tensile modulus—1 300 000 psi (8966 MPa).

Flexural strength, ultimate—22 000 psi (152 MPa).

Flexural modulus—1 000 000 psi (6897 MPa).

Glass content—30 %.

Thickness—0.30 in. (7.62 mm).

5. Materials

5.1 Resin Matrix System:

5.1.1 The resin shall be determined to be acceptable for the service either by test, see 8.6, or by verified case history.

5.1.2 *Catalyst/Promoter System*, shall be as recommended or approved by the resin producer.

5.1.3 *Diluents*, such as added styrene, fillers, dyes, pigments, or flame retardants shall be used only when agreed upon between the fabricator and the buyer. When such items are required, limits for each shall be agreed upon between the fabricator and the buyer. A thixotropic agent may be added to the resin for viscosity control.

NOTE 8—The addition of fillers, dyes, pigments, flame retardants, and thixotropic agents may interfere with visual inspection of laminate quality.

NOTE 9—Chemical resistance can be significantly affected by the catalyst/promoter system, diluents, dyes, fillers, flame retardants, or thixotropic agent used in the resin.

5.1.4 *Resin Pastes*, used where necessary to fill crevices formed by joining subassemblies before overlay shall not be subject to the limitations of 5.1.3. Pastes shall be made with thixotropic agents.

5.1.5 *Ultraviolet Absorbers*, may be added to the exterior surface for improved weather resistance when agreed upon between the fabricator and the buyer.

5.2 Fiber Reinforcement:

5.2.1 *Surfacing Mat (veil)* is a thin mat of fine fibers used primarily to produce a smooth surface on a reinforced plastic.

TABLE 3 Classification System for Hand Lay-up Laminates Using Minimum Property Values^A

Classification Order											
RTP followed by:											
(1)	Type	I	II	III	IV	V					
(2)	Class	P	V	followed by FS (), if specified with flame spread in parentheses in accordance with Test Method E 84				
		Polyester	Vinylester								
Physical and Mechanical Properties											
(3)	Grade	1	2	3	4	5	6	7	8	9	0
1st Digit:	Tensile strength, ultimate psi × 10 ³ (MPa)	9 (62)	11 (76)	13 (90)	15 (104)	17.5 (121)	20 (138)
2nd Digit:	Tensile modulus, tangent psi × 10 ³ (MPa)	0.85 (5 863)	0.95 (6 552)	1.05 (7 242)	1.15 (7 932)	1.3 (8 966)	1.5 (10 346)	1.75 (12 070)	2.0 (13 794)
3rd Digit:	Flexural strength, ultimate psi × 10 ³ (MPa)	16 (110)	18 (124)	20 (138)	22 (152)	24 (166)
4th Digit:	Flexural modulus, psi × 10 ⁶ (MPa)	0.7 (4 828)	0.85 (5 863)	1.0 (6 897)	1.15 (7 932)	1.3 (8 966)	1.5 (10 346)
5th Digit:	Glass content, by weight, %	25	28	30	34	37	40	44

^A Table will be completed as new resins and higher strength laminates become available.

5.2.1.1 Veil shall be determined to be acceptable for the service either by Test Methods C 581 or D 3681, or by a verified case history.

5.2.1.2 Requirements of acceptable surface veils are:

- (a) Resin compatibility,
- (b) Uniform fiber distribution,
- (c) Single filaments (not bundled),
- (d) The thickness shall be a minimum of 10 mils per ply when saturated with resin, and
- (e) Minimum fiber length shall be 0.5 in.

NOTE 10—The chemical resistance of the RTP laminate is provided by the resin. In combination with the cured resin, the surfacing veil helps determine the thickness of the resin-rich layer, reduces microcracking, and provides a nonwicking chemically resistant layer.

Additional desirable considerations in choosing a veil for a specific application include:

- (a) Drapability (surfacing veil should conform to mold shape),
- (b) Dry and wet tensile strength,
- (c) Binder solubility (if used),
- (d) Wetability,
- (e) Surfacing veil shall wet-out completely without trapping air during laminating, and
- (f) Surfacing veil should not inhibit resin cure.

5.2.2 *Chopped-Strand Mat*, shall be “E” or “ECR” type glass fiber, $1\frac{1}{2}$ oz/ft² (459 g/m²), with sizing and binder compatible with the resin.

5.2.3 *Woven Roving*, shall be “E” or “ECR” type glass, $24\frac{1}{2}$ oz/yd² (832 g/m²), 5 by 4 square weave fabric having a sizing compatible with the resin.

5.2.4 *Roving*, used in chopper guns for spray-up application, shall be “E” or “ECR” type glass with sizing compatible with the resin.

5.2.5 *Other Reinforcements*, such as nonwoven biaxial or unidirectional fabric. These products shall be a commercial grade of “E” or “ECR” type glass fiber with a sizing that is compatible with the resin.

5.3 Laminates:

5.3.1 Laminate construction shall be in accordance with the tabulated lay-up sequence for the specified type.

5.3.2 *Type I*, laminate structure is detailed in Table 1.

5.3.3 *Type II*, laminate structure is detailed in Table 2.

6. Laminate Fabrication

6.1 Apply the catalyzed resin to a mold or mandrel properly prepared with a parting agent or film suitable for the lay-up resin. Next apply the specified surface mat, rolling so as to draw the resin through the mat for thorough wet-out and deaeration.

6.2 Apply resin and two plies of $1\frac{1}{2}$ -oz (42.6-g) mat. As an alternative, a minimum of two passes of chopped roving (minimum fiber length 1 in. (25.4 mm) and resin may be applied by the spray-up process equivalent in weight and thickness to 3 oz/ft² (918 g/m²) of chopped mat. Each pass of chopped roving or ply of chopped-strand mat shall be thoroughly rolled out. This section of the laminate shall be allowed to exotherm prior to application of subsequent plies of reinforcement.

6.3 Continue lay-up in the sequence of plies, tabulated for the specified laminate type. Roll each ply for thorough wet-out and deaeration.

6.3.1 Interruption of laminate construction for exotherm shall follow instructions noted on Table 1 and Table 2 for the particular laminate type. The final ply of reinforcement before interruption for exotherm shall be $1\frac{1}{2}$ -oz/ft² (459-g/m²) mat or chopped roving equivalent. The initial ply of the following lamination shall be $1\frac{1}{2}$ -oz/ft² mat or chopped roving equivalent.

6.4 The outer surface of the fabricated laminate shall be smooth and free of exposed glass fibers. The final ply shall be mat or chopped roving equivalent. A surfacing mat is not required unless specified. Surface resin may require the addition of paraffin or may be sealed with overlaid film, as required or approved by the resin producer, to ensure proper surface cure.

6.4.1 When pigmentation is specified, the pigment shall be incorporated only in the resin used to lay-up the final laminate ply.

6.5 All edges of reinforcement material except surfacing mat shall be lapped 1-in. (25.4-mm) minimum. Lapped edges of adjacent layers shall be staggered. Surfacing mat shall be butted together or have overlaps no more than $\frac{1}{2}$ in. (12.7 mm). Gaps are not permitted.

7. Physical and Mechanical Properties

7.1 The composition and sequence requirements for Type I and II laminates are shown in Table 1 and Table 2.

7.2 The mechanical property requirements for Type I and II laminates are shown in Table 4.

7.3 Physical properties of each type and grade of laminate shall be established on flat laminates prepared under shop conditions. In Type II laminates the woven roving is to be laid square, and test specimens are to be cut parallel to the warp rovings.

7.3.1 Test specimens cut from fabricated equipment usually are not parallel to warp rovings. Interpretation of mechanical property data obtained from such specimens is discussed in Appendix X1.

8. Test Methods

8.1 *Tensile Strength and Tangent Modulus of Elasticity*—Test Method D 638.

8.1.1 Specimens shall be in accordance with Type III, Fig. 1 of Test Method D 638 for all laminate thicknesses.

8.2 *Flexural Strength and Tangent Modulus of Elasticity*—Test Methods D 790, Method I, Procedure A, and Table 1, $1/d = 16$ to 1.

8.2.1 Specimens shall be the full thickness of the laminate as fabricated.

8.2.2 The loading nose shall be applied to the inner face of the laminate specimen.

8.3 *Glass Content*—Test Method D 2584.

8.3.1 The residual, undisturbed glass-fiber plies from the ignition shall be separated carefully and counted to confirm standard lay-up sequence.

8.4 *Thickness* shall be measured with a ball-foot micrometer.



TABLE 4 Standard Laminate Properties

Calculated Thickness, ^A in. (mm)	Type	Tensile ^B		Mechanical Properties, min, psi (MPa) ^C		
		Ultimate Stress × 10 ⁻³ (MPa)	Modulus × 10 ⁻⁶ (MPa)	Flexural ^D		Edge Compression ^E
				Ultimate Stress × 10 ⁻³ (MPa)	Modulus × 10 ⁻⁶ (MPa)	
ALL	I	9.0 (62)	0.85 (5862)	16.0 (110)	0.7 (4828)	16 (110)
0.22 (5.6)	II	12.0 (83)	0.9 (6207)	19.0 (131)	0.8 (5518)	16 (110)
0.30 (7.6)	II	13.5 (93)	1.1 (7587)	20.0 (138)	0.9 (6207)	18 (124)
0.37 (9.4) and up	II	15.0 (104)	1.2 (8276)	22.0 (152)	1.0 (6897)	20 (138)

^A The thickness shall be not less than 90 % of the calculated thickness shown.

^B Test Method D 638.

^C Barcol hardness should be 90 % (minimum) of cast resin hardness.

^D Test Method D 790.

^E Test Method D 695.

8.5 Hardness—Test Method D 2583.

8.6 Chemical Resistance—Test Method C 581.

8.6.1 Exposure tests under plant operating conditions shall employ Test Method C 581 standard test laminate samples.

NOTE 11—Thicker laminates shall not be used for such tests, as results will vary significantly compared to exposure of standard samples in Test Method C 581.

8.7 Surface Flame-Spread Classification—Test Method E 84.

9. Workmanship and Finish

9.1 The finished laminate shall conform to visual acceptance criteria of Table 5.

TABLE 5 Visual Acceptance Criteria

Visual Observation	Surface Inspected	
	Process Side	Nonprocess Side
Cracks	None	None
Crazing (fine resin-rich surface cracks)	None	Maximum dimension 1 in. (25.4 mm). Maximum density 5/ft ² (0.1 m ²). ^A
Blisters (rounded elevations of the laminate surface over bubbles)	None	Maximum 1/4 -in. (6.4-mm) diameter by 1/8 in. (3.2 mm) high. Maximum 2/ft ² (2/0.1 m ²). ^A
Wrinkles and solid blisters	Maximum deviation, 20 % of wall thickness, but not exceeding 1/8 in. (3.2 mm). ^A	Maximum deviation, 20 % of wall thickness, but not exceeding 3/16 in. (4.8 mm). ^A
Pits (craters in the laminate surface)	Maximum dimensions, 1/8 -in. (3.2-mm) diameter by 1/32 in. (0.8 mm) deep. Maximum number 10/ft ² (10/0.1 m ²). ^A	Maximum dimension 1/8 -in. (3.2-mm) diameter by 1/16 in. (1.6 mm) deep. Maximum density 10/ft ² (10/0.1 m ²). ^A
Surface porosity, pin holes, or pores in the laminate	Maximum dimensions, 1/16 -in. (1.6-mm) diameter by 1/32 in. (0.8 mm) deep. Maximum number 20/ft ² (20/0.1 m ²) by 1/16 in. (1.6 mm). Must be resin-rich. ^A	Maximum dimension 1/16 -in. (1.6-mm) diameter by 1/16 in. deep. Maximum number 20/ft ² (20/0.1 m ²). Must be resin-rich. ^A
Chips (small piece broken from edge or surface)	Maximum dimensions, 1/8 -in. (3.2-mm) diameter by 1/32 in. (0.8 mm) deep. Maximum number 1/ft ² (1/0.1 m ²). ^A	Maximum dimension 1/4 -in. (6.4-mm) diameter by 1/16 in. (1.6 mm) deep. Maximum number 5/ft ² (5/0.1 m ²). ^A
Dry spot (non-wetted reinforcing)	None	Maximum dimensions 2 in. ² (13 cm ²) per ft ² (0.1 m ²). ^A
Entrapped air (bubbles or voids or delaminations in the laminate)	Maximum diameter 1/16 in. (1.6 mm), 10/in. ² (10/6.5 cm ²) maximum density. Maximum diameter 1/8 in. (3.2 mm), 2/in. ² (2/6.5 cm ²) maximum density. Maximum depth of 1/32 in. (0.8 mm). ^{AB}	Maximum diameter 1/16 in. (1.6 mm), 10/in. ² (10/6.5 cm ²) maximum density. Maximum diameter 1/8 in. (3.2 mm), 2/in. ² (2/6.5 cm ²) maximum density. Maximum diameter 3/16 in. (4.8 mm), 2/ft ² (2/0.1 m ²). Maximum density. ^{AB}
Exposed glass	None	None
Burned areas	None	None
Exposure of cut edges	None ^C	None ^C
Scratches	None over 0.005 in. deep and 4 in. long	Maximum length 12 in. (3.5 mm). Maximum depth 0.010 in. (0.25 mm) 2/ft ² (2/0.1 m ²), maximum density. ^A
Foreign matter	None	1/8 -in. (3.2-mm) diameter, maximum density 1/ft ² (1/0.1 m ²). 3/16 -in. (4.8-mm) diameter, maximum density 1/ft ² (1/0.1 m ²). ^{AD}

^A Maximum 5 % of total surface area affected.

^B Entrapped air or bubbles described are allowed, provided the surface cannot easily be broken with a pointed object, such as a knife blade.

^C Cut edges must be covered with resin.

^D Foreign matter must not penetrate the surface and must not contribute to entrapped air or other defects not allowed.

9.2 The surface exposed to the chemical environment (process side) shall be smooth, resin-rich, and fully cured. The exterior surface shall also be fully cured.

9.2.1 The degree of cure shall be measured by a Barcol hardness test in accordance with Test Method D 2583. At least 80 % of the random readings shall exceed at least 90 % of the resin manufacturer's recommended hardness for the cured resin.

9.2.2 Potential air-inhibited, undercured surfaces (both interior secondary lamination and exterior non-mold surfaces)

shall be tested using an acetone sensitivity test. Four to five drops of acetone rubbed with a finger on the laminate surface, free of mold release, wax, dust, or dirt, until it evaporates, will not result in surface softness or tackiness.

10. Keywords

10.1 contact molded; corrosion-resistant equipment; glass-fiber-reinforced; laminate; reinforced thermosetting plastic (RTP); thermoset polyester resin; thermoset vinyl ester resin

APPENDIXES

(Nonmandatory Information)

X1. INTERPRETATION OF DATA FROM ANISOTROPIC LAMINATES

X1.1 *General*—Mechanical properties of laminates containing alternative plies of woven roving and chopped strand mat are dependent upon relationship between the direction of

the applied load and the direction of the roving strands. For 5 by 4 square weave roving, the approximate relationship is shown in Fig. X1.1.

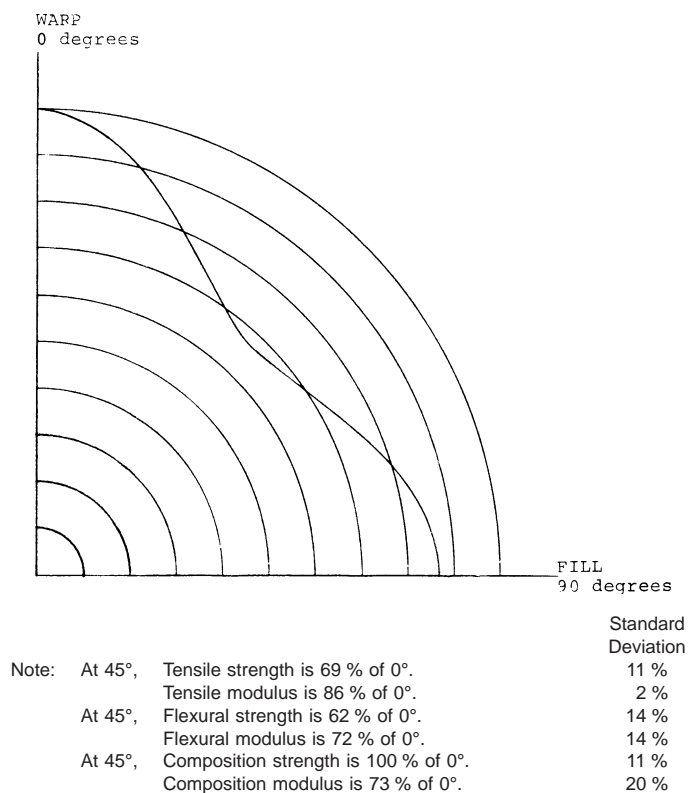


FIG. X1.1 Directional Properties of RTP Alternating Mat/Woven Roving

X2. QUALIFICATION OF LAMINATE STRUCTURE FOR TYPE, CLASS, AND GRADE DESIGNATION

X2.1 *General*—The RTP laminate structures other than those covered by this specification may be characterized for designation as standard type, class, and grade by means of the following procedure.

X2.2 *Laminate Preparation:*

X2.2.1 Under shop fabrication conditions, lay up 12 by 25-in. (305 by 635-mm) flat laminates of the proposed laminate structure in nominal thicknesses of $\frac{3}{16}$, $\frac{5}{16}$, $\frac{1}{2}$, and $\frac{3}{4}$ in. (4.8, 8, 12.8, and 19.2 mm).

X2.2.1.1 Orientation of reinforcing fibers of fabrics shall be such as to produce maximum properties in the 25-in. (635-mm) direction of the laminate.

X2.2.1.2 Laminates having essentially unidirectional fiber reinforcement shall be 25 by 25-in. (635 by 635-mm) size to provide sufficient laminate for testing in two directions.

X2.2.1.3 The degree of cure of the surface exposed to the chemical environment (process side) shall be measured by a Barcol hardness test in accordance with Test Method D 2583. At least 80 % of the random readings shall exceed at least 90 % of the resin manufacturer's recommended hardness for the cured resin.

X2.2.1.4 Cured laminates shall be flat within the limits of $\frac{1}{8}$ -in./ft (3.2-mm/0.1 m²) deviation from a plane surface.

X2.3 *Testing:*

X2.3.1 Tests shall be performed, and results certified, by a recognized independent testing laboratory experienced in the testing of RTP laminates.

X2.3.2 Determine mechanical and physical properties as required by Sections 7 and 8 of this specification.

X2.3.2.1 Unidirectional laminates, as described in X 2.2.1.2, shall have properties determined both parallel to, and at 90° to, the direction of reinforcement.

X2.4 *Report:*

X2.4.1 The report shall describe laminate manufacture, date of manufacture, resin used with batch number noted, identification of reinforcements used, cure components, additives, and all pertinent cure information.

X2.4.2 The report shall contain the data obtained on all specimens, the laboratory that performed the tests, and the date performed.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).