

Specification for

**Scheduling,
dimensioning, bending
and cutting of steel
reinforcement for
concrete**

UDC 666.982.24:693.554.1:669.14.018.291:[658.512 + 531.71]

NO COPYING WITHOUT BSI PERMISSION EXCEPT AS PERMITTED BY COPYRIGHT LAW



Committees responsible for this British Standard

The preparation of this British Standard was entrusted by the Iron and Steel Standards Policy Committee (ISM/-) to Technical Committee ISM/9, upon which the following bodies were represented:

British Cement Association
 British Independent Steel Producers' Association
 British Precast Concrete Federation Ltd.
 British Reinforcement Manufacturers' Association
 British Steel Industry
 British Steel Industry (Wire Section)
 Concrete Society
 County Surveyors' Society
 Department of the Environment (Property Services Agency)
 Department of Transport
 Electricity Supply Industry in England and Wales
 Fabric Reinforcement Development Association
 Federation of Civil Engineering Contractors
 High Yield Bar Development Association
 Institution of Civil Engineers
 Institution of Structural Engineers
 UK Certification Authority Reinforcing Steels

This British Standard, having been prepared under the direction of the Iron and Steel Standards Policy Committee, was published under the authority of the Board of BSI and comes into effect on 31 July 1989

© BSI 12-1998

First published, June 1969
 First revision May 1981
 Second revision July 1989

The following BSI references relate to the work on this standard:
 Committee reference ISM/9
 Draft for comment 88/38680 DC

ISBN 0 580 17289 9

Amendments issued since publication

Amd. No.	Date of issue	Comments
6311	February 1990	Indicated by a sideline in the margin

Contents

	Page
Committees responsible	Inside front cover
Foreword	ii
<hr/>	
1 Scope	1
2 Definitions	1
3 Notations	1
4 Form of schedule	2
5 Form of bar or fabric label	11
6 Dimensions	11
7 Scheduling	12
8 Bends and hooks	13
9 Tolerances on cutting and bending dimensions	13
10 Radius of bending	14
11 Bending of fabric reinforcement	14
12 Fabrication and routine inspection	15
<hr/>	
Appendix A Inspection and certification	17
<hr/>	
Figure 1 — Scheduled fabric	3
Figure 2 — Form of bar schedule	4
Figure 3 — Form of fabric schedule	5
Figure 4 — Bar label	11
Figure 5 — Dimensioning of an acute angle	13
Figure 6 — Dimensioning of cranked bars	14
Figure 7 — Example of bar with more than one bend	14
Figure 8 — Position of welded transverse wires	16
<hr/>	
Table 1 — Preferred shapes, their method of measurement and calculation of length	6
Table 2 — Other shapes, their method of measurement and calculation of length	8
Table 3 — Minimum former radii, bend and hook allowances	12
Table 4 — Cutting and bending tolerances	14
Table 5 — Radius bending: maximum values requiring bending	15
<hr/>	
Publications referred to	Inside back cover
<hr/>	

Foreword

This British Standard has been prepared under the direction of the Iron and Steel Standards Policy Committee and is a revision of BS 4466:1981, which is withdrawn.

This British Standard applies to reinforcement complying with BS 4449, BS 4482, BS 4483 and BS 6744.

The purpose of this standard is to ensure uniformity of practice in the scheduling of steel for the reinforcement of concrete. To establish a clear and unambiguous system for scheduling, it is necessary to specify the method of indicating dimensions and the order in which the information is given on the schedule.

A major difference between this edition of BS 4466 and previous editions is that shape codes 60, 81, 72, 73, 74 and 86, which are specified by their internal dimensions, have been deleted and replaced by shape codes 61, 82, 77, 78, 79 and 87, which are specified by their external dimensions. Shape code 83 has been deleted.

Product testing and certification. Attention is drawn to the provision in this British Standard of a facility for third party certification of product conformity with this British Standard based on testing and continuous product surveillance coupled with assessment of a supplier's quality systems against BS 5750-2.

Enquiries as to the availability of third party certification schemes and of competent test laboratories will be forwarded by BSI to the Association of Certification Bodies. If a third party certification scheme does not already exist, users should consider approaching an appropriate body from the list of Association members.

A British Standard does not purport to include all the necessary provisions of a contract. Users of British Standards are responsible for their correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

Summary of pages

This document comprises a front cover, an inside front cover, pages i and ii, pages 1 to 18, an inside back cover and a back cover.

This standard has been updated (see copyright date) and may have had amendments incorporated. This will be indicated in the amendment table on the inside front cover.

1 Scope

This British Standard specifies requirements for the scheduling, dimensioning, bending and cutting of steel reinforcement complying with BS 4449, BS 4482, BS 4483 and BS 6744.

NOTE The titles of publications referred to in this standard are listed on the inside back cover.

2 Definitions

For the purposes of this British Standard the following definitions apply.

2.1

bar

a steel product of any cross section complying with BS 4449 or BS 6744

2.2

wire

a steel product of any cross section complying with BS 4482

2.3

size

the nominal size of a bar or wire in millimetres

NOTE This is given the symbol “*d*”.

2.4

nominal size

the diameter of a circle with an area equal to the effective cross-sectional area of the bar or wire

2.5

mark number

an identifying number (which also appears on the delivery label) cross-referencing individual line entries on the schedule to the detailed-drawing

2.6

shape code

a two-digit coded definition of the reinforcement shape as given in Table 1 and Table 2

2.7

pitch

the centre-to-centre spacing of bars or wires in a sheet of fabric or the longitudinal spacing of turns in a helix

2.8

mesh

the rectangle defined by the pitch of the longitudinal wires and the pitch of the cross wires in a sheet of fabric

2.9

fabric

a factory-made product of welded bars or wires complying with BS 4483

NOTE There are three categories of fabric as defined in 2.10 to 2.12.

2.10

designated fabric

fabric reinforcement where the wire and mesh arrangement can be defined by an identifiable fabric reference

NOTE The British Standard range of preferred fabrics (see Table 1 of BS 4483:1985) exemplifies designated fabrics.

2.11

scheduled fabric

fabric reinforcement with a regular wire and mesh arrangement that can be defined by specifying the size and spacing in each direction using the notation shown in Figure 1, which assumes that sheets are always viewed with their cross wires uppermost

2.12

detailed fabric

fabric reinforcement not covered by the definitions in 2.10 and 2.11

NOTE A dimensioned drawing is required to define the mesh arrangement.

2.13

fabric reference

an alpha numeric code defining the wire sizes and mesh dimensions of a sheet of designated fabric

3 Notations

The type and grade of reinforcement shall be abbreviated using the following letters.

- | | |
|---|---|
| R | grade 250 reinforcement complying with BS 4449 |
| T | grade 460 type 2 reinforcement complying with BS 4449 or BS 4482 |
| S | stainless reinforcement complying with the grade and type selected from BS 6744 |
| W | grade 460 plain reinforcement complying with BS 4482 |
| D | grade 460 type 1 reinforcement complying with BS 4482 |
| X | reinforcement of a type not included in the above list having material properties that are defined in the design or contract specification. |

4 Form of schedule

4.1 For bar reinforcement, the form of schedule shown in Figure 2 shall used.

NOTE The schedule should be referred to as a “bar schedule” since it is customary for the reinforcement fabricator to prepare separate cutting and bending lists for fabrication. The bar schedule is usually completed in sequence of structural units, whereas the cutting and bending lists are usually sorted into type and size of bar.

For cutting and bending purposes, schedules shall be provided on separate sheets of paper of size A4 of BS 4000 and not as part of the detailed reinforcement drawings.

Fabric reinforcement shall be specified on the fabric schedule form shown in Figure 3.

When used for detailed fabric, the schedule shall include a cross-reference to the relevant dimensional drawing.

4.2 For schedules that are not produced on a computer, the minimum width of the columns in the bar and fabric schedules shall be as shown in Figure 2 and Figure 3.

For computer produced schedules, the column widths and the size of the schedule may vary from those shown in Figure 2 and Figure 3, but the sequence of columns shall be maintained. The schedule shall not be significantly larger than size A4 of BS 4000.

4.3 The schedule reference shall appear at the top right-hand corner of the schedule form and shall comprise consecutive numbers, which include a cross-reference to the drawing. Such terms as “sheet number” or “page number” shall not be used. The styles “1 (of 6)” and “6 (and last)” may be used on manually prepared schedules but the words in parentheses shall not form part of the schedule reference.

The first three characters of the schedule reference shall be the last three characters of the drawing number, starting at, for example, drawing number 001. The schedule number shall occupy the fourth and fifth spaces, starting at 01 and not exceeding 99 for any one drawing. The sixth space shall be used for schedule revision letters.

Example:

	Drawing	Schedule	Revision
Bar schedule reference	0 4 6	0 3	A


NOTE Where a schedule revision is necessary, the line or lines affected may be indicated by a suitable reference on the schedule, e.g. “A” at the right-hand side of the schedule in Figure 2.

If a job contains more than 999 drawings it can be broken down into groups by the use of a job number, e.g. job number 1234A foundations and job number 1234B ground floor.

4.4 The bar or fabric schedule shall include the statement “This schedule complies with BS 4466”.

4.5 The bar or fabric mark shall comprise simple and consecutive numbers or letters with a maximum of six characters. Where special end preparation is required (e.g. for couplers), the bar mark shall commence with “E”.

4.6 In the “Type and size” column, the notations specified in clause 3 for the type and grade of bar shall be given and this shall be followed by the nominal size of the bar in millimetres.

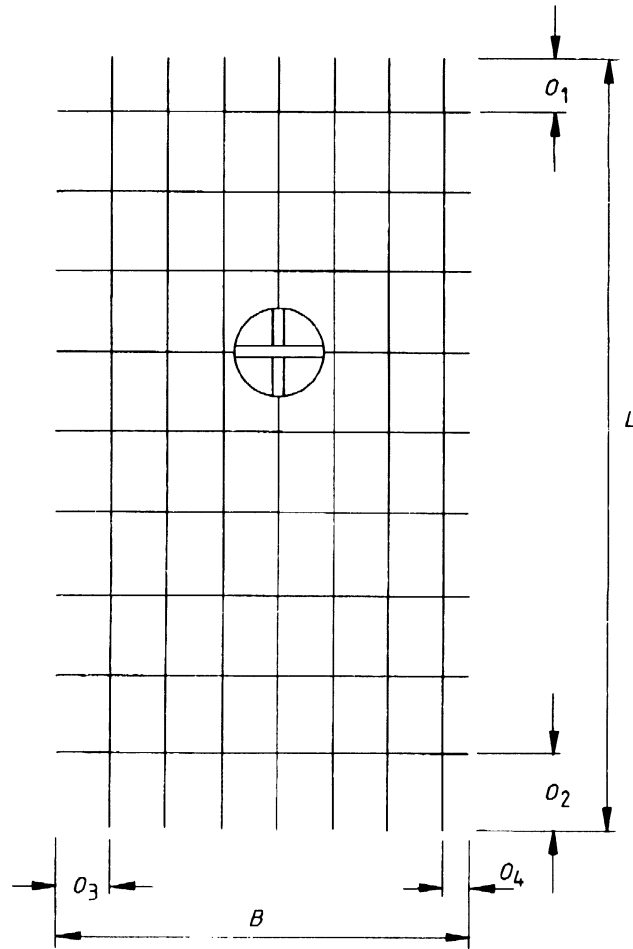**Key**

L is the length of the longitudinal wires (which are not necessarily the longer wires in the sheet).

B is the length of the cross wires.

O_1 and O_2 are the overhangs of the longitudinal wires.

O_3 and O_4 are the side overhangs of the cross wires.

Figure 1 — Scheduled fabric

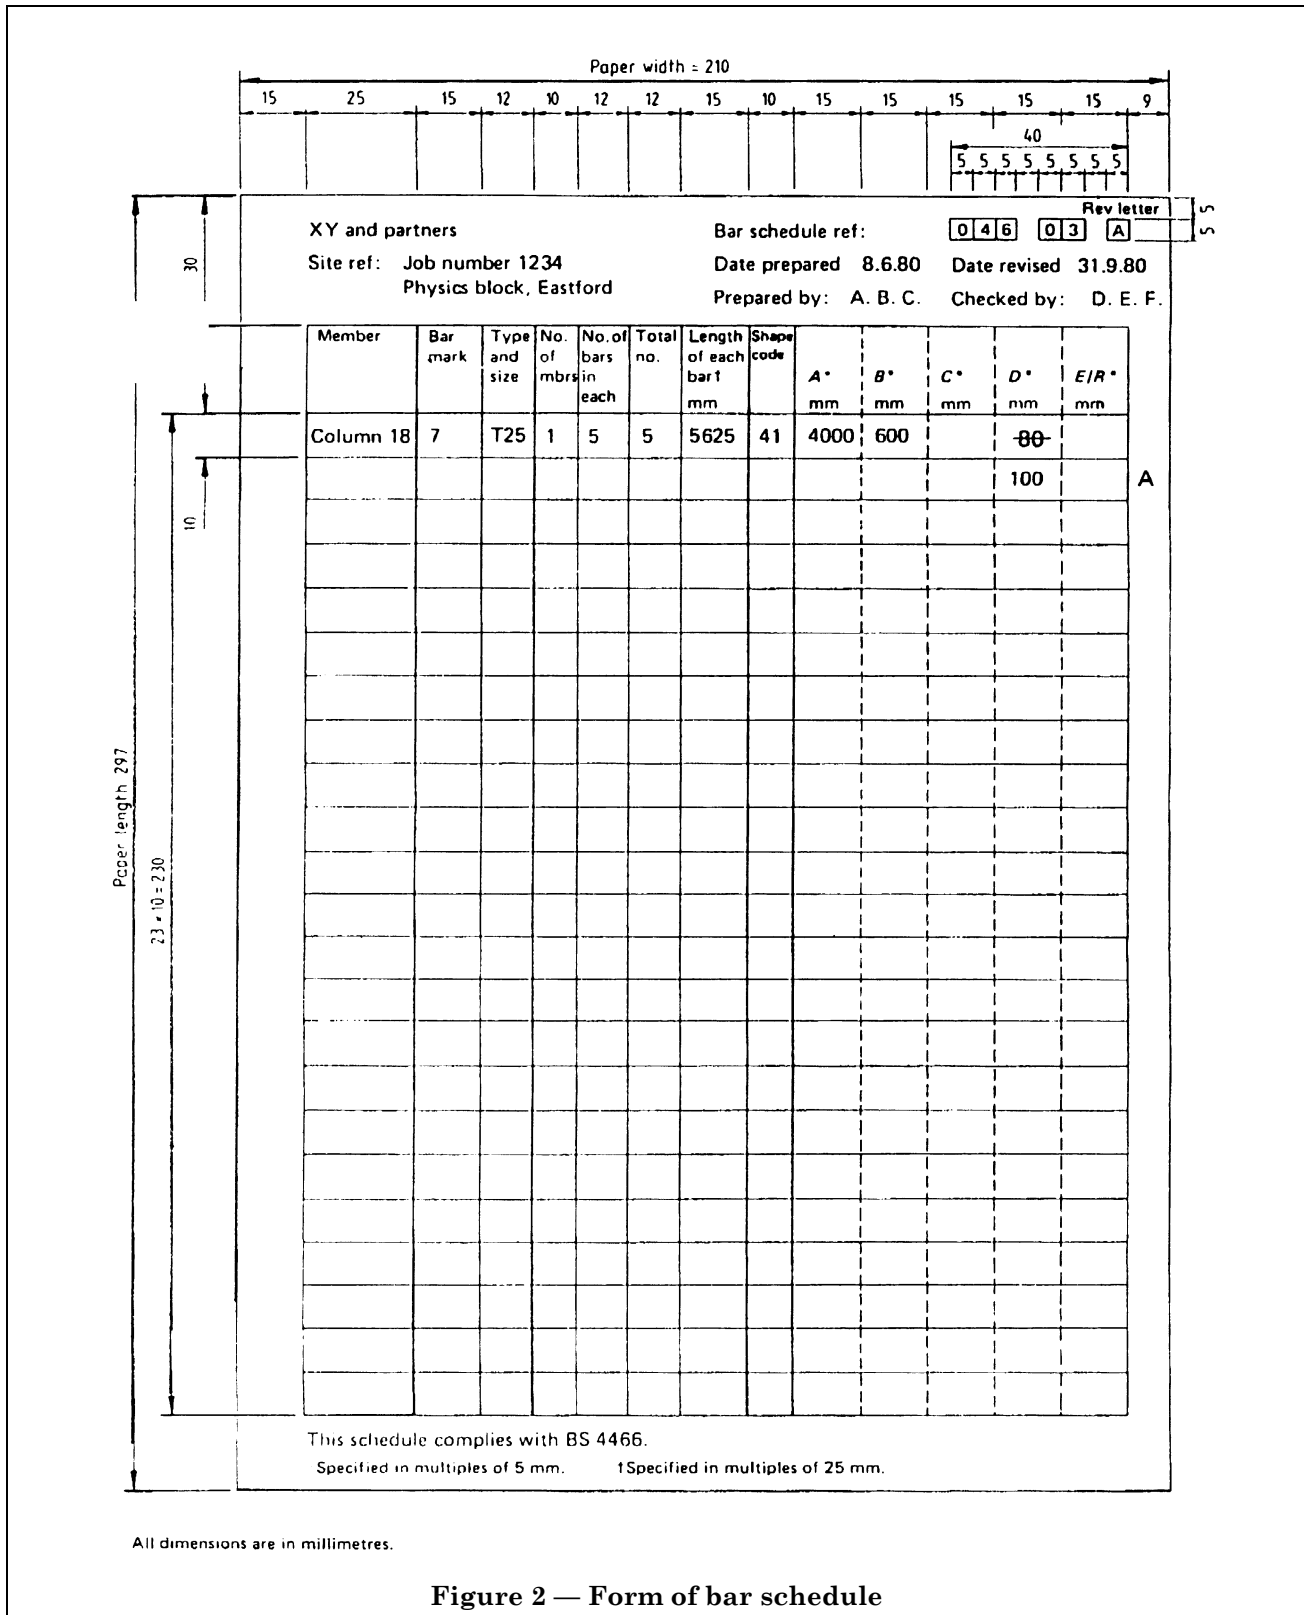


Figure 2 — Form of bar schedule

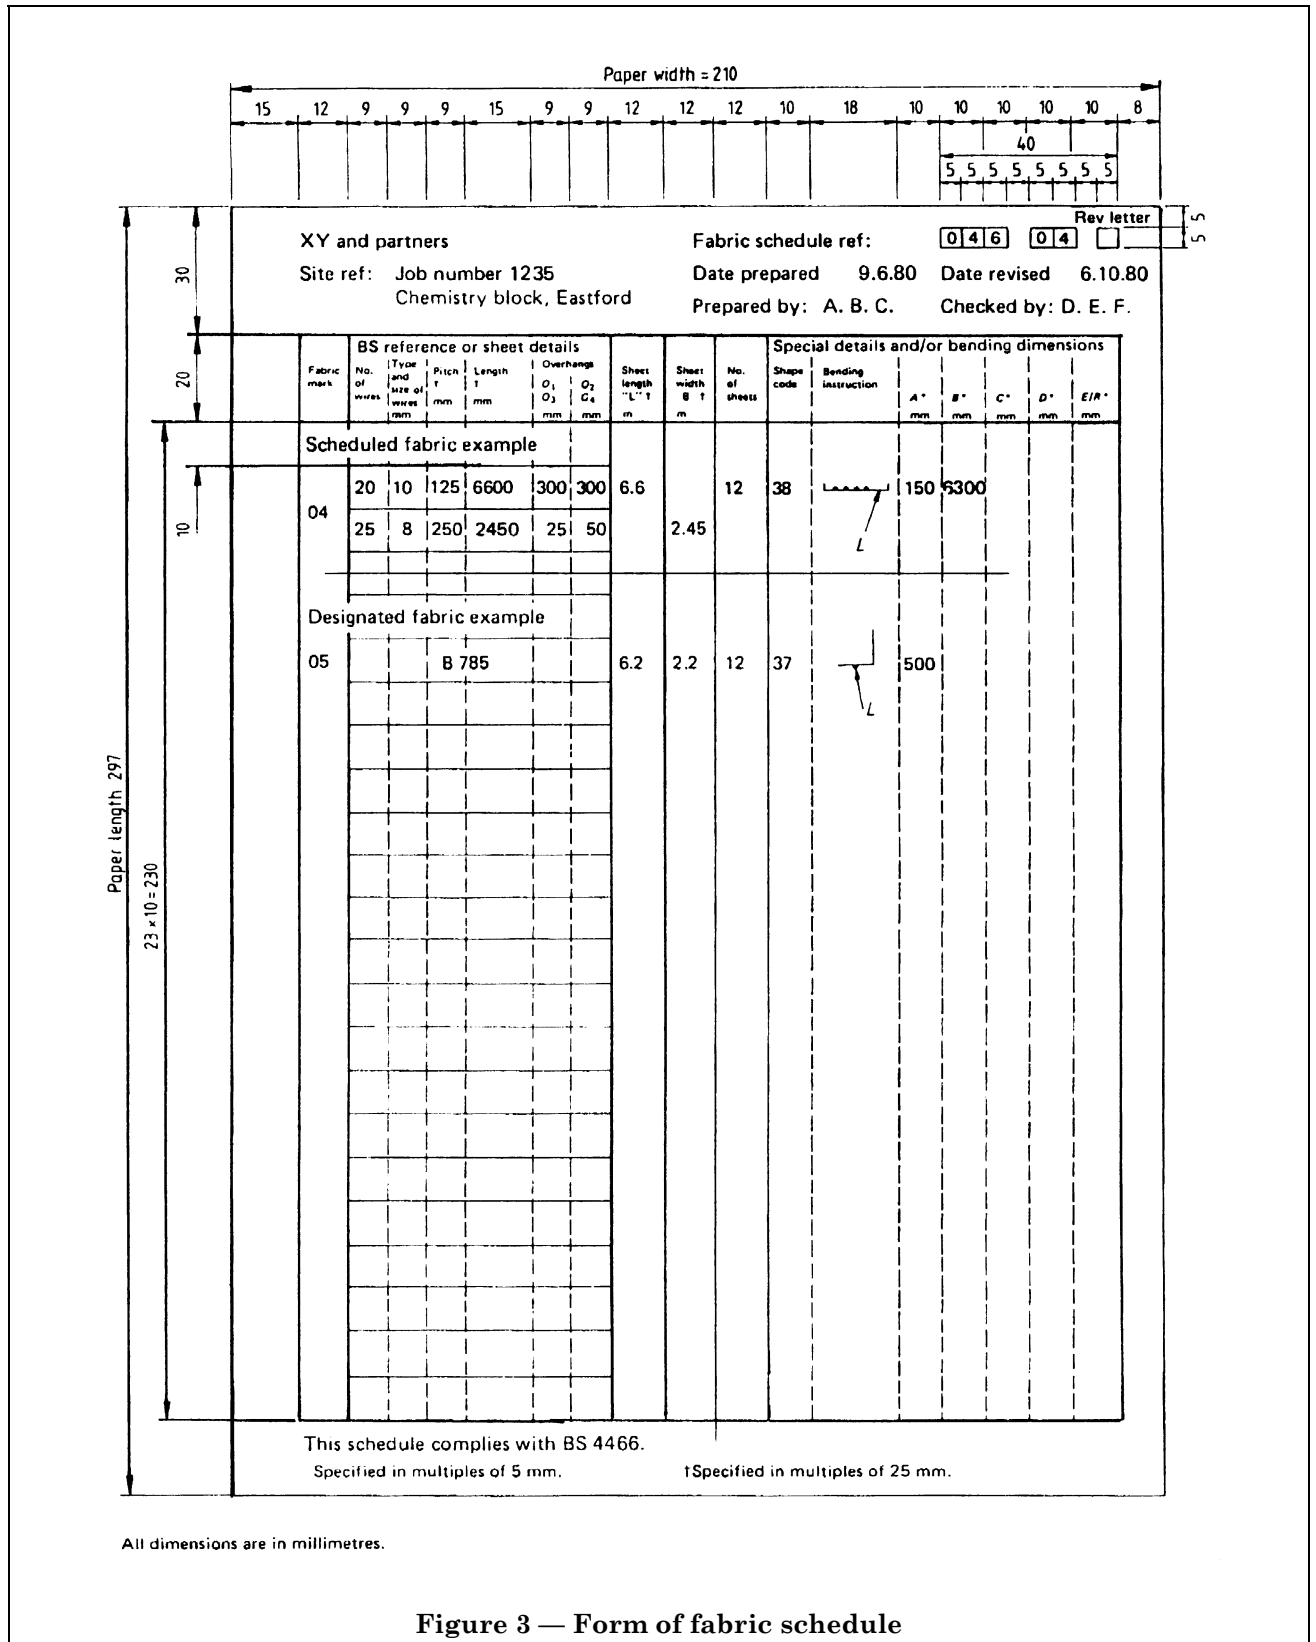


Figure 3 — Form of fabric schedule

Table 1 — Preferred shapes, their method of measurement and calculation of length


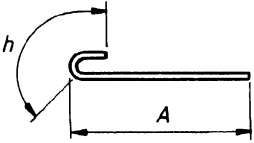
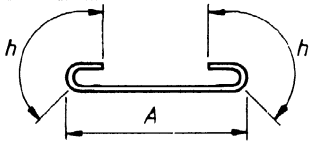




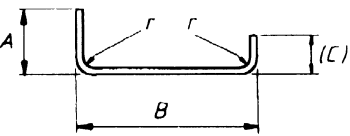
Shape code	Method of measurement of bending dimensions	Total length of bar (L) measured along centreline
20		A mm
32		$A + h$
33		$A + 2h$
34		$A + n$ Where the overall dimension of the bob is critical, use shape code 37
35		$A + 2n$ Where the overall dimension of either bob is critical, do not use this shape code
37	 or 	$A + (B) - \frac{1}{2} r - d$ This formula is approximate Where r is greater than the minimum value in Table 3 use shape code 51
38		$A + B + (C) - r - 2d$

Table 1 — Preferred shapes, their method of measurement and calculation of length

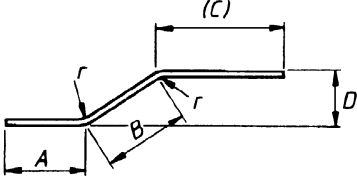
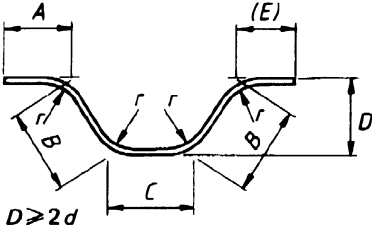
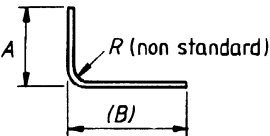

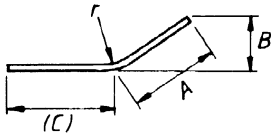
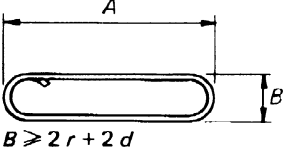
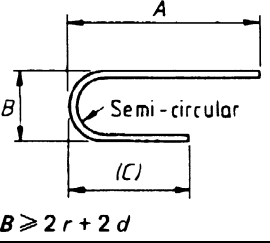
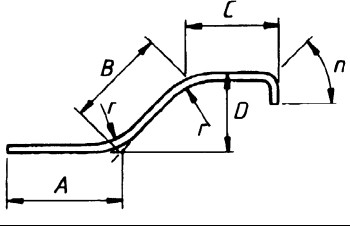
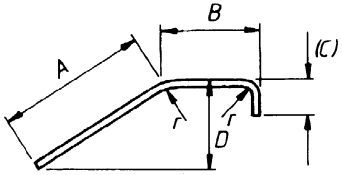
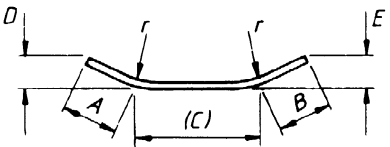
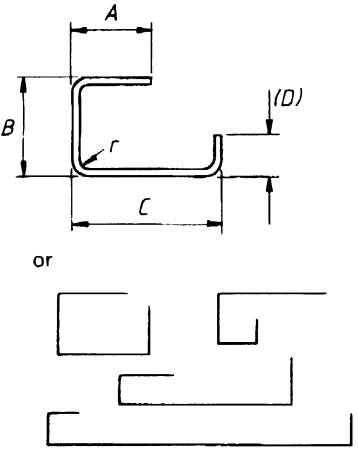
Shape code	Method of measurement of bending dimensions	Total length of bar (L) measured along centreline
41	 <p>$D \geq 2d$</p>	<p style="text-align: center;">mm</p> <p>If angle with the horizontal are 45° or less, $A + B + (C)$ See note 4</p>
43	 <p>$D \geq 2d$</p>	<p>If angle with the horizontal are 45° or less, $A + 2B + C + (E)$ See note 4</p>
51	 <p>R (non standard)</p>	$A + (B) - \frac{1}{2}R - d$ This formula is approximate If R is minimum, use shape code 37 If R is greater than 200 mm, see note 2 to clause 10
61		$2(A + B) + 12d$ Neither A nor B are to be less than $12d$ or 150 mm, which ever is the greater, for grade 460 in size not exceeding 20 mm nor less than $14d$ for size of 25 mm and over Neither A nor B are to be less than $10d$ for grade 250 with a minimum value of A and B of 100 mm See note 3
62		<p>If angle with the horizontal is 45° or less, $A + (C)$ See note 4</p>
82	 <p>$B \geq 2r + 2d$</p>	$2A + 3B + 18d$ If B is greater than $400 + 2d$, See note 2 to clause 10 See note 3
<p>NOTE 1 r indicates the minimum value in Table 3.</p> <p>NOTE 2 The dimensions in parentheses are the free dimensions.</p> <p>NOTE 3 To avoid separate equations for each steel grade and bending radius, simplified total length formulae are used for shape codes 61 and 82. These formulae are necessarily approximate.</p> <p>NOTE 4 The length formula is approximate and when bending angles exceed 45° the length should be calculated more accurately allowing for the difference between the specified overall dimensions and the true length measured along the central axis of the bar or wire.</p>		

Table 2 — Other shapes, their method of measurement and calculation of length

Shape code	Method of measurement of bending dimensions	Total length of bar (<i>L</i>) measured along centreline
39	 <p>$B \geq 2r + 2d$</p>	mm $A + 0.57B + (C) - 1.57d$ If <i>B</i> is greater than $400 + 2d$, see note 2 to clause 10
42		If angle with horizontal is 45° or less, $A + B + C + n$ See note 4
45		If angle with horizontal is 45° or less, $A + B + (C) - \frac{1}{2}r - d$ See note 4
49		If angle with horizontal is 45° or less, $A + B + (C)$ See note 4
52	 <p>or</p>	$A + B + C + (D) - 1\frac{1}{2}r - 3d$

Licensed Copy: Sheffield University, University of Sheffield, 25 March 2003, Uncontrolled Copy, (c) BSI

Table 2 — Other shapes, their method of measurement and calculation of length

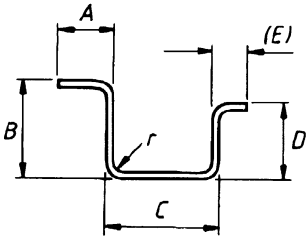
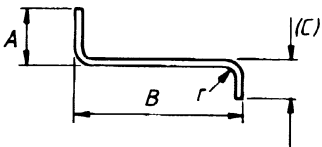
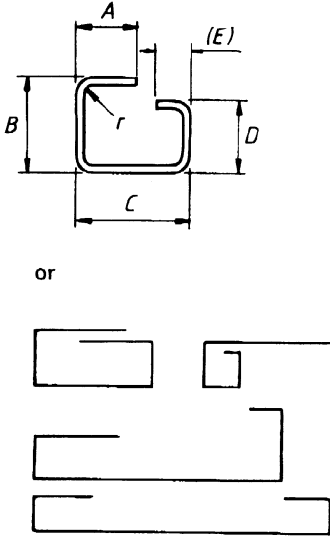
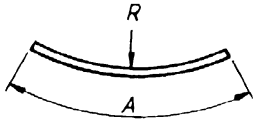
Shape code	Method of measurement of bending dimensions	Total length of bar (L) measured along centreline
53		$A + B + C + D + (E) - 2r - 4d$ <p style="text-align: center;">mm</p>
54		$A + B + (C) - r + 2d$
55		$A + B + C + D + (E) - 2r - 4d$
65	 <p>These bars will be supplied straight when the radius is greater than that given in table 5</p>	A

Table 2 — Other shapes, their method of measurement and calculation of length

Shape code	Method of measurement of bending dimensions	Total length of bar (L) measured along centreline
77		$2A + B + 20d$ See note 3 mm
78		$2A + B + C + 3d$ See note 3
79		$2A + 3B + 10d$ Neither A nor B are to be less than $12d$ or 150 mm, whichever is the greater, for grade 460 in sizes not exceeding 20 mm nor less than $14d$ for sizes of 25 mm and over. Neither A nor B are to be less than $10d$ for grade 250 with a minimum value of A and B of 100 mm See note 3
85		$A + B + 0.57 C + (D) - \frac{1}{2}r - 2.57d$ If C is greater than $400 + 2d$, see note 2 to clause 10
87		Where B is not greater than $A/5$ $\frac{C}{B}\pi(A - d)$ ($L \leq 12$ m) where A is the external diameter (in mm) B is the pitch of helix (in mm) C is the overall height of helix (in mm) Where B is greater than $A/5$ the formula does not apply. There shall be at least two full turns in the helix. NOTE Unless A is small relative to d , this shape is fabricated in a closed form and pulled to shape on site.

Table 2 — Other shapes, their method of measurement and calculation of length

Shape code	Method of measurement of bending dimensions	Total length of bar (L) measured along centreline
99	All other shapes	<p style="text-align: center;">mm</p> <p>To be calculated</p> <p>A dimension sketch shall be drawn out over schedule columns <i>A</i> to <i>E</i>. Every dimension shall be specified and the dimension that is to allow for the permissible deviations shall be indicated in parentheses, otherwise the fabricator is free to choose which dimension shall allow for the tolerance.</p> <p>If a shape that is given in this Table 1 is required but a different dimension is to allow for the permissible deviations, the shape shall be drawn out and given the shape code 99 and the free dimension shall be indicated in parentheses. The tolerances given in Table 4 also apply.</p>

NOTE 1 r indicates the minimum value in Table 3.
NOTE 2 The dimensions in parentheses are the free dimensions.
NOTE 3 To avoid separate equations for each steel grade and bending radius simplified total length formulae are used for shape codes 77, 78 and 79. These formulae are necessarily approximate.
NOTE 4 The length formula is approximate and when bending angles exceed 45 ° the length should be calculated more accurately allowing for the difference between the specified overall dimensions and the true length measured along the central axis of the bar or wire. When the bending angles approach 90 °, it is preferable to specify shape code 99 with a fully dimensional sketch.

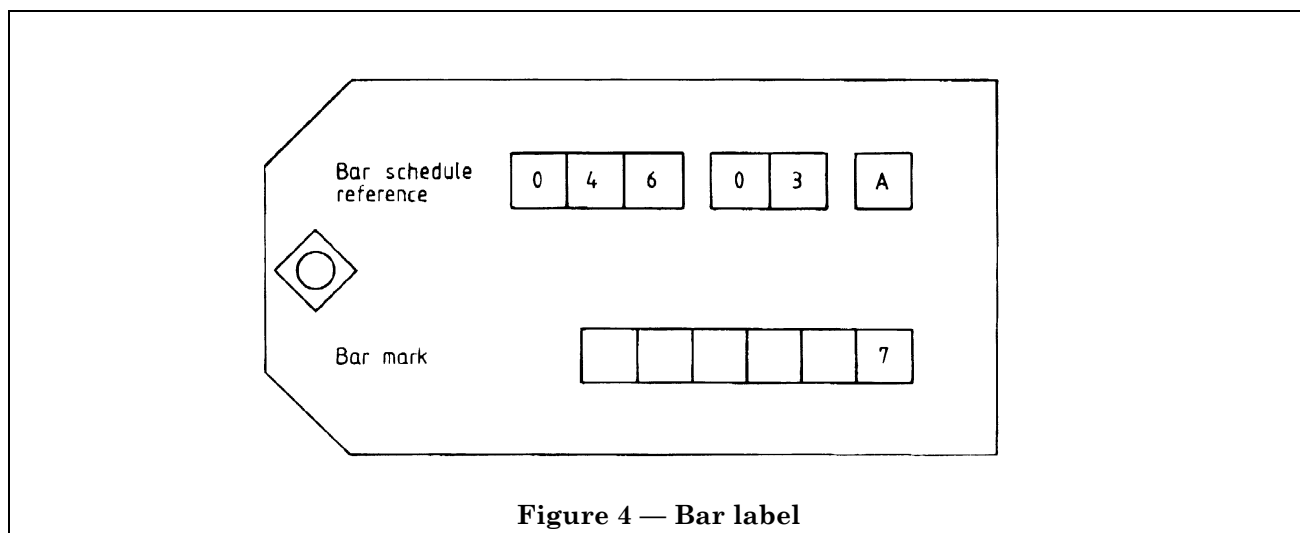


Figure 4 — Bar label

5 Form of bar or fabric label

The schedule reference and the mark given in the “Bar (or fabric) mark” column of the schedule shall be put on the labels attached to the reinforcement.

Apart from any information required by the supplier for his own identification and internal system, no other information shall appear on the label.

Figure 4 shows an example of a bar label, which gives information that is given in Figure 2.

6 Dimensions

6.1 The total length dimension specified on the schedule for each bar or for wires in each sheet of fabric shall be rounded up to a multiple of 25 mm.

6.2 The dimensions for the scheduling of reinforcement bounded by two concrete faces shall allow for the permissible deviations.

6.3 The dimensions for the scheduling of reinforcement requiring special end preparation shall take into account the system to be used.

6.4 The dimensions given on the schedule shall be measured as shown in Table 1 and Table 2 where, for deformed reinforcement, the outside surface shall be the extremities of the deformation.

6.5 To facilitate packing for transportation, each bent bar shall be contained in an imaginary rectangle, the shorter side of which shall be not longer than 2 750 mm.

NOTE Normally the total length should not exceed 12 m, although longer lengths may be obtained by special arrangement with the supplier. The upper limit is determined by handling and transportation and should not exceed 18 m for bars.

6.6 The values for minimum radii, bend and hook allowances (r , n and h respectively as given in Table 3) shall apply to all shape codes except that larger values may apply for shape code 99. For shape codes 51 and 65, where the radius R is scheduled, R shall be not less than r .

7 Scheduling

7.1 Each bar or sheet of fabric shall be scheduled completely and without reference to earlier schedules. Such descriptions as "See schedule 12" or "As before" shall not be used.

7.2 The preferred shape codes to be used shall be as given in Table 1. Table 2 gives other shape codes that may be required.

Shapes that do not have a specific shape code number given in Table 1 or Table 2 shall be coded as "99", in accordance with Table 2.

7.3 For shapes without an end anchorage, the dimension shown in parentheses in Table 1 and Table 2 shall be the variable dimension to allow for the permissible deviations.

NOTE The dimension in parentheses in Table 1 and Table 2 may be omitted from the schedule.

If a different dimension is required to be the free variable, the shape shall be drawn and given the shape code 99.


7.4 No dimension given in Table 1 or Table 2 shall be given a zero value, as this changes the basic shape.

Table 3 — Minimum former radii, bend and hook allowances


Bar size d	Type and grade R and type and grade S			Type and grade T and type and grade S			Fabric complying with BS 4483			
	r	n	h	r	n	h	d	r	n	h
6 ^a	12	100	100	18	100	100	5	15	100	100
8	16	100	100	24	100	100	6	18	100	100
10	20	100	100	30	100	110	7	21	100	100
12	24	100	110	36	100	140	8	24	100	100
16	32	100	150	48	100	180	9	27	120	135
20	40	100	180	60	110	220	10	30	120	135
25	50	130	230	100	180	350	12	36	130	145
32	64	160	290	128	230	450	—	—	—	—
40	80	200	360	160	280	560	—	—	—	—
50 ^a	100	250	450	200	350	700	—	—	—	—

NOTE 1 The use of hooks as end anchorages is not normally necessary with deformed bars.
NOTE 2 See clause 8 for definition of y .
^a These are non-preferred sizes.

Bend (bob)

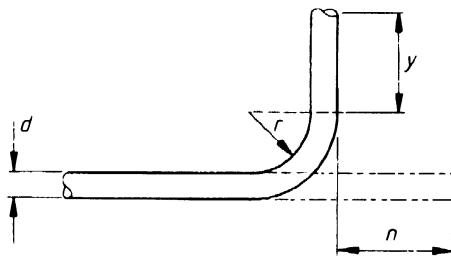

Hook

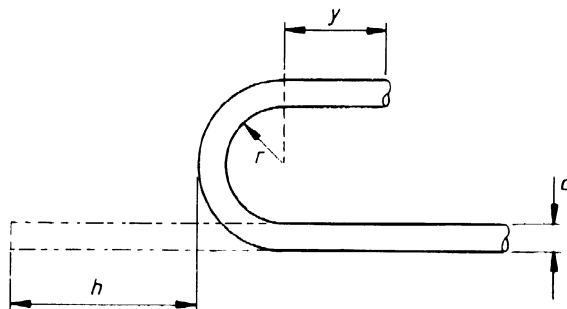


7.5 Shapes with shape code 99 shall be drawn on the schedule over columns A to E using two parallel lines to indicate the reinforcement thickness, and the origin of projected surface intersection lines shall be used for dimensions. The methods of measurement shall be in accordance with those shown in Table 1 and Table 2 and **7.6** to **7.11** shall be complied with. The total length shall be given and, unless there is an end anchorage bend or hook, one bending dimension, preferably an end dimension, shall be indicated in parentheses as the free dimension to allow for the permissible deviations. The r , n and h values shall be given on the schedule if they differ from the values given in Table 3. The tolerances given in Table 4 shall also apply to shape code 99.

7.6 If the angle between two portions of the shape meeting at a bend is not a right angle, it shall be given and shall be defined by co-ordinates and not by degrees of arc.

7.7 Any shape including an acute angle shall be classified as a 99 shape code and drawn out in full with construction lines.

NOTE The shape codes given in Table 1 and Table 2 do not include an acute angle.

When dimensioning an acute angle the tangential lines shown in Figure 5 shall be used.

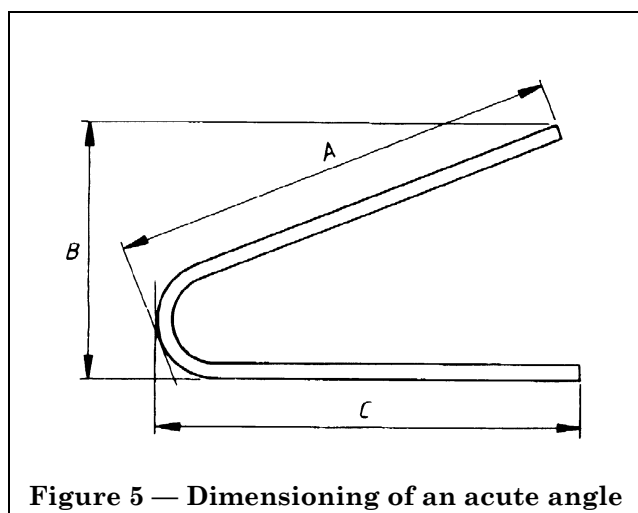

7.8 Bars bent in two planes shall be sketched isometrically or shown in two elevations, using first angle projection in accordance with BS 308-1. The words “bent in two planes” or “isometric view” shall appear on the schedule.

7.9 The overall off-set dimension of a crank shall be not less than twice the size of the bar or wire. The angled length as shown in Figure 6 shall be not less than $10d$ for grade 250 nor less than $12d$ for grade 460 in sizes of less than 20 mm nor less than $14d$ for grade 460 in sizes of 25 mm and over.

7.10 For all shapes with two or more bends in the same or opposite directions (whether in the same plane or not), the overall dimension given on the schedule shall always include a minimum straight of $4d$ between the curved portion of the bends, as shown in Figure 7. The value of x in Figure 7 shall be not less than the following:

- $10d$ for grade 250 material;
- $12d$ for grade 460 material not exceeding sizes of 20 mm;
- $14d$ for grade 460 material in sizes of 25 mm and over.

NOTE The minimum values of x are expressed in terms of the nominal size of the reinforcement. In practice, rolling and bending tolerances, and the fact that the circumscribing diameter of deformed reinforcement may be up to 10 % greater than the nominal size, need to be considered. For example, the actual overall dimension of a hook bent in accordance with Table 1 is greater than $2r + 2d$ and similarly two bends including a $4d$ straight have an actual overall x value greater than $2r \pm 6d$.

7.11 The minimum length of material to be given on the schedule to form a bend or hook shall be as given for n or h respectively in Table 3.

NOTE The reason for this is that existing bending equipment requires such a minimum length for the rotating pin to engage with the bar and bend it round the standard former. In giving this length on the schedule, due consideration should be given to the possibility of negative cutting tolerances (up to 25 mm) reducing the actual length of material. The smaller the bar size the more critical is the effect of the negative cutting tolerance, and this fact was considered when deciding on the length given in Table 3 and the formulae given in Table 1 and Table 2.

8 Bends and hooks

NOTE 1 Minimum former radii are given in Table 3.

NOTE 2 The overall dimension of a bend may vary from the design dimension by up to the sum of the cutting deviations (± 25 mm) and the cumulative bending deviations.

Before taking into account the cumulative cutting tolerances, the nominal value for y in Table 3 shall be calculated as follows:

- for a bend, $n - 0.57r + 0.21d$;
- for a hook, $h - 2.14r - 0.57d$

9 Tolerances on cutting and bending dimensions

The tolerances given in Table 4 shall apply for cutting and/or bending dimensions and shall be taken into account when completing the schedule. The end anchorage or the dimension in parentheses in the shape codes given in Table 1 and Table 2 shall be used to allow for any permissible deviations resulting from cutting and bending.

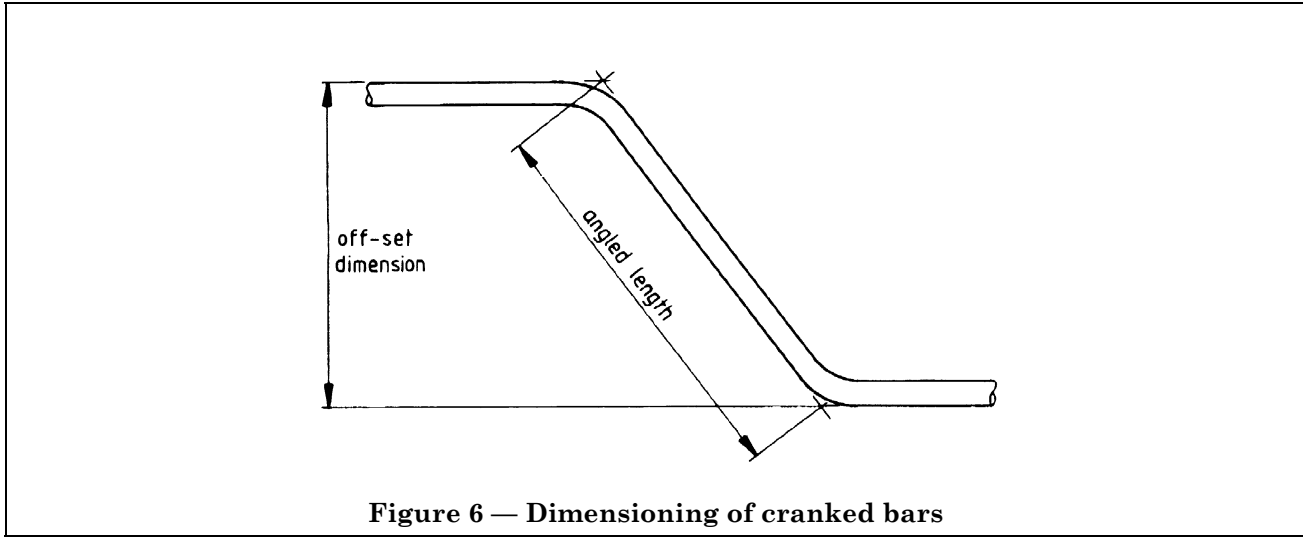


Figure 6 — Dimensioning of cranked bars

10 Radius of bending

Reinforcement to be formed to a radius exceeding that given in Table 5 shall be supplied straight.

NOTE 1 The required curvature may be obtained during placing.

NOTE 2 For shapes with straight and curved lengths (e.g. shape codes 39, 51, 82 and 85) the largest practical radius for the production of a continuous curve is 200 mm, and for larger radii the curve may be produced by a series of short straight sections.

11 Bending of fabric reinforcement

NOTE The schedule for fabric reinforcement (see Figure 3) includes a column headed "Bending instruction" for the additional information that is required when specifying bent fabric. The three-dimensional characteristic of fabric reinforcement can give rise to ambiguities that are best overcome by means of a simple sketch in the "Bending instruction" column.

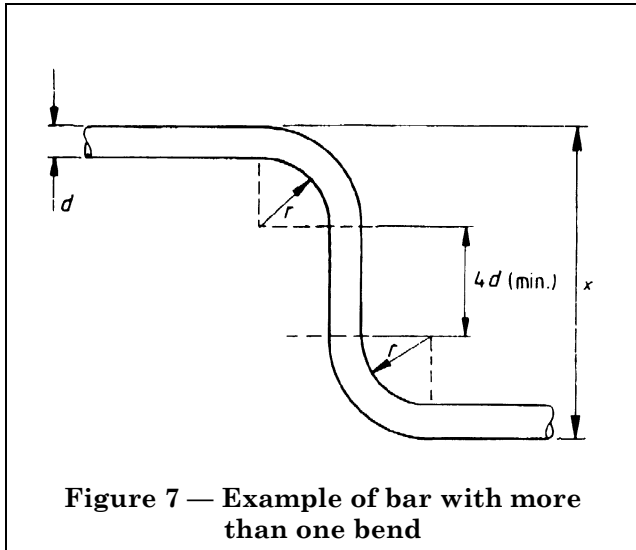


Figure 7 — Example of bar with more than one bend

Table 4 — Cutting and bending tolerances


	Tolerance
	mm
Cutting of straight lengths (including reinforcement for Subsequent bending)	+ 25 - 25
Bending ≤ 1 000	+ 5 - 5
> 1 000 mm to ≤ 2 000 mm	+ 5 - 10
> 2 000 mm	+ 5 - 25

Table 5 — Radius bending: maximum values requiring bending


Bar size (mm)	—	6	—	8	—	10	12	16	20	25	32	40
Wire size (mm)	5	6	7	8	9	10	12	—	—	—	—	—
Radius (m)	2.4	2.5	2.6	2.75	3.0	3.5	4.25	7.5	14.0	30.0	43.0	58.0

The sketch in the “Bending instruction” column shall indicate the following.


(a) The direction of bending relative to the transverse wires



(b) The direction of the longitudinal wires of the sheet to ensure bending about the correct axis



(c) The correct orientation of an asymmetric sheet to ensure the correct setting out of bending dimensions



Sheet with unequal overhangs.

For all bent fabric reinforcement, the bending dimensions shall avoid welded transverse wires occurring within four diameters of the start of a bend (see Figure 8).

12 Fabrication and routine inspection

12.1 Fabrication

12.1.1 Cutting to length shall be carried out using purpose-made shearing equipment. The tolerances given in Table 4 shall apply to each length.

12.1.2 Bending shall be carried out on power bending machines. Plain smooth surfaces or rolls that do not offer resistance to longitudinal movement to the bars or fabric being bent shall be provided to ensure adequate support. The minimum former radii used in bending for the appropriate type and size of reinforcement shall be as given in Table 3.

12.1.3 The fabricator shall ensure that cutting and bending machine operatives are trained in the skills necessary to produce cut and bent products of consistent quality within the permissible size deviations. A formal operative approval and testing system shall be implemented and operatives shall have been certified by the fabricator as having achieved minimum standards of competence.

12.2 Routine inspection

Routine inspection shall be carried out in accordance with the following clauses:

- a) **A.1**; and
- b) either of the following:
 - i) for material covered by a third party certification scheme, **A.2**; or
 - ii) for material not covered by a third party certification scheme, **A.3**.

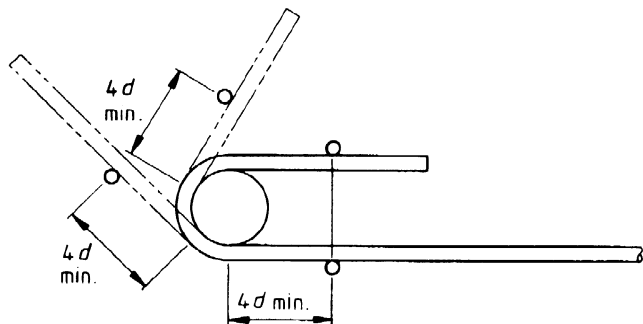


Figure 8 — Position of welded transverse wires

Appendix A Inspection and certification

A.1 Fabricator's inspection

A.1.1 Extent of inspection

The fabricator shall carry out inspections of the following parameters of the schedules and of specimens of cut lengths and bent items at a frequency in accordance with A.1.2.

- a) *Cut lengths*
 - i) The bar or fabric mark (see 4.5).
 - ii) The type and size of the specimens and the type and size given on the schedule (see 4.6).
 - iii) The length of the specimens and the length given on the schedule (see clause 9).
- i) *Bent items*
 - i) The bar or fabric mark (see 4.5).
 - ii) The type and size of the specimens and the type and size given on the schedule (see 4.6).
 - ii) The shape of the specimens and the shape code given on the schedule (see 7.2 to 7.7).
 - iii) The diameter of former used (by checking the bar) (see 12.1.2 for radii).
 - iv) The length of the specimens and the length given on the schedule (see clause 9).

A.1.2 Frequency

The fabricator shall inspect daily and inspection records shall be retained for 10 years. Specimens shall be selected at random from a representative range of output items at the following frequency.

Where the output of the fabrication unit over the preceding full working week is less than 75 t	At least 10 specimens per day
Where the output of the fabrication unit over the preceding full working week is between 75 t and 150 t	At least 20 specimens per day
Where the output of the fabrication unit over the preceding full working week is greater than 150 t	At least 40 specimens per day

Where no records are available covering the preceding full working week, the lesser of either 40 specimens per day or the total output per day shall be inspected.

For inspection purposes, not more than 50 % of the specimens shall be selected from items having an identical bar mark.

If any of the specimens that are inspected are found to have parameters that do not comply with the appropriate requirements all the other bars or fabrics with the same mark number (or numbers) shall be inspected and they shall all comply with the appropriate requirements.

A.2 Fabricated material covered by a third party product certification scheme

A.2.1 Consistency of production

For the purposes of determining the consistency of production, the long term quality level shall be assessed at regular intervals. No conclusions regarding compliance with this British Standard shall be made on the basis of this assessment.

A.2.2 Determination of the long term quality level

The third party certification authority shall assess the long term consistency of production (fabrication) by examining the fabricator's inspection records at regular intervals. No more than 5 % of the items inspected shall have failed to comply with the requirements before rectification.

A.3 Fabricated material not covered by a third party product certification scheme

A.3.1 General

Material not covered by a third party product certification scheme shall be assessed by acceptance tests on each batch. Sampling and testing shall be carried out by an independent organization at the producer's works or in the stockholder's yard.

A.3.2 Extent of sampling and inspection/testing

For the purposes of inspection/testing, the delivery shall be subdivided into test units with a maximum mass of 10t.

Specimens shall be taken from each test unit as follows:

- a) 15 specimens (if appropriate 60 specimens) of cut lengths;
- b) 15 specimens (if appropriate 60 specimens) of bent items.

A.3.3 Inspection by attributes

The following parameters of the schedule and of the specimens taken in accordance with **A.3.2** shall be inspected.

- a) *Cut lengths*
 - i) The bar or fabric mark (see **4.5**).
 - ii) The type and size of the specimens and the type and size given on the schedule (see **4.6**).
 - iii) The length of the specimens and the length given on the schedule (see clause **9**).
- b) *Bent items*
 - i) The bar mark (see **4.5**).
 - ii) The type and size of the specimens and the type and size given on the schedule (see **4.6**).
 - iii) The shape of the specimens and the shape code given on the schedule (see **7.2** to **7.7**).
 - iv) The diameter of former used (by checking the bar) (see **12.1.2** for radii).
 - v) The length of the specimens and the length given on the schedule (see clause **9**).

A.3.4 Evaluation of results

All the parameters inspected in accordance with **A.3.3** for all the 15 specimens shall comply with the appropriate requirements.

If a maximum of two of the 15 results do not comply, a further 45 specimens shall be assessed so that a total of 60 specimens is assessed. The test unit shall be deemed to comply with this standard if no more than two of the 60 results do not comply with the appropriate requirements.

Publications referred to

BS 308, *Engineering drawing practice*.

BS 308-1, *Recommendations for general principles*.

BS 4000, *Specification for sizes of paper and board*.

BS 4449, *Specification for carbon steel bars for the reinforcement of concrete*.

BS 4482, *Specification for cold reduced steel wire for the reinforcement of concrete*.

BS 4483, *Specification for steel fabric for the reinforcement of concrete*.

BS 5750, *Quality systems*¹⁾.

BS 5750-2, *Specification for production and installation*.

BS 6744, *Specification for austenitic stainless steel bars for the reinforcement of concrete*.

BS 8110, *Structural use of concrete*.

BS 8110-1, *Code of practice for design and construction*.

¹⁾ Referred to in the foreword only.

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover. Tel: 020 8996 9000. Fax: 020 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: 020 8996 9001. Fax: 020 8996 7001.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre. Tel: 020 8996 7111. Fax: 020 8996 7048.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration. Tel: 020 8996 7002. Fax: 020 8996 7001.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

If permission is granted, the terms may include royalty payments or a licensing agreement. Details and advice can be obtained from the Copyright Manager. Tel: 020 8996 7070.

BSI
389 Chiswick High Road
London
W4 4AL