

Products and systems for the protection and repair of concrete structures — Test methods —

Part 1: Determination of linear shrinkage for polymers and surface protection systems (SPS)

The European Standard EN 12617-1:2003 has the status of a
British Standard

ICS 91.080.40

National foreword

This British Standard is the official English language version of EN 12617-1:2003.

The UK participation in its preparation was entrusted by Technical Committee B/517, Concrete, to Subcommittee B/517/8, Protection and repair of concrete structures, which has the responsibility to:

- aid enquirers to understand the text;
- present to the responsible international/European committee any enquiries on the interpretation, or proposals for change, and keep the UK interests informed;
- monitor related international and European developments and promulgate them in the UK.

A list of organizations represented on this subcommittee can be obtained on request to its secretary.

Cross-references

The British Standards which implement international or European publications referred to in this document may be found in the *BSI Catalogue* under the section entitled “International Standards Correspondence Index”, or by using the “Search” facility of the *BSI Electronic Catalogue* or of British Standards Online.

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard does not of itself confer immunity from legal obligations.

This British Standard was published under the authority of the Standards Policy and Strategy Committee on 16 May 2003

Summary of pages

This document comprises a front cover, an inside front cover, the EN title page, pages 2 to 6, an inside back cover and a back cover.

The BSI copyright notice displayed in this document indicates when the document was last issued.

Amendments issued since publication

Amd. No.	Date	Comments

© BSI 16 May 2003

ISBN 0 580 41898 7

English version

Products and systems for the protection and repair of concrete structures - Test methods - Part 1: Determination of linear shrinkage for polymers and surface protection systems (SPS)

Produits et systèmes pour la protection et la réparation des structures en béton - Méthodes d'essai - Partie 1: Détermination du retrait linéaire des polymères et des systèmes de protection de surface

Produkte und Systeme für den Schutz und die Instandsetzung von Betontragwerken - Prüfverfahren - Teil 1: Bestimmung des linearen Schrumpfes von Polymeren und Oberflächenschutzsystemen (OS)

This European Standard was approved by CEN on 3 March 2003.

CEN members are bound to comply with the CEN/CENELEC Internal Regulations which stipulate the conditions for giving this European Standard the status of a national standard without any alteration. Up-to-date lists and bibliographical references concerning such national standards may be obtained on application to the Management Centre or to any CEN member.

This European Standard exists in three official versions (English, French, German). A version in any other language made by translation under the responsibility of a CEN member into its own language and notified to the Management Centre has the same status as the official versions.

CEN members are the national standards bodies of Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Slovakia, Spain, Sweden, Switzerland and United Kingdom.



EUROPEAN COMMITTEE FOR STANDARDIZATION
COMITÉ EUROPÉEN DE NORMALISATION
EUROPÄISCHES KOMITEE FÜR NORMUNG

Management Centre: rue de Stassart, 36 B-1050 Brussels

Contents

	page
Foreword.....	3
1 Scope	4
2 Normative references	4
3 Terms and definitions	4
4 Apparatus	4
5 Sampling	5
6 Procedure	6
7 Precision	6
8 Test report	6

Foreword

This document (EN 12617-1:2003) has been prepared by Technical Committee CEN/TC 104 "Concrete and related products", the secretariat of which is held by DIN.

This European Standard shall be given the status of a national standard, either by publication of an identical text or by endorsement, at the latest by October 2003, and conflicting national standards shall be withdrawn at the latest by October 2003.

The European Standard is one of a series dealing with products and systems for the protection and repair of concrete structures:

EN 12617-1, *Products and systems for the protection and repair of concrete structures - Test methods - Part 1: Determination of linear shrinkage for polymers and surface protection systems (SPS)*.

EN 12617-2, *Products and systems for the protection and repair of concrete structures - Test methods - Determination of shrinkage of polymer for injection products - Part 2: Shrinkage of crack injection product formulated with polymer binder: volumetric shrinkage*.

EN 12617-3, *Products and systems for the protection and repair of concrete structures - Test methods - Part 3: Determination of early age linear shrinkage for structural bonding agents*.

EN 12617-4, *Products and systems for the protection and repair of concrete structures - Test methods - Part 4: Determination of shrinkage and expansion*.

According to the CEN/CENELEC Internal Regulations, the national standards organizations of the following countries are bound to implement this European Standard: Austria, Belgium, Czech Republic, Denmark, Finland, France, Germany, Greece, Hungary, Iceland, Ireland, Italy, Luxembourg, Malta, Netherlands, Norway, Portugal, Slovakia, Spain, Sweden, Switzerland and the United Kingdom.

1 Scope

This European Standard specifies a method for determining the linear shrinkage of solvent free multicomponent cold curing reactive resins for the protection and repair of concrete structures.

NOTE The method is not suitable for rubber, elastic and very fast curing products. Rubber and elastic products show relaxation effects and can dissipate stress to the ground. For testing very fast curing products the pot life should be long enough for mixing and preparing the test specimens.

2 Normative references

This European Standard incorporates by dated or undated references, provisions from other publications. These normative references are cited at the appropriate places in the text, and the publications are listed hereafter. For dated references, subsequent amendments to or revisions of any of these publications apply to this European Standard only when incorporated in it by amendment or revision. For undated references the latest edition of the publication referred to applies (including amendments).

EN 1504-1, *Products and systems for the protection and repair of concrete structures – Definitions, requirements, quality control and evaluation of conformity – Part 1: Definitions.*

EN ISO 15528, *Paints, varnishes and raw materials for paints and varnishes – Sampling (ISO 15528:2000).*

EN ISO 1513, *Paints and varnishes – Examination and preparation of samples for testing (ISO 1513:1992).*

3 Terms and definitions

For the purposes of this European Standard, the terms and definitions contained in EN 1504-1 and the following apply.

3.1 shrinkage

contraction in length or volume during curing of the material

3.2 shrinkage value

ratio of the gap width in mm after curing to the original length of 1 m


4 Apparatus

4.1 Two trough sections, of length $1\,000\text{ mm} \pm 1\text{ mm}$, made of $30\text{ mm} \times 4\text{ mm}$ steel angle with ends fitted with flat ground flanges closed with matching bolted metal plates which also serve as supports, all shown in Figures 1 and 2.

4.2 Instrument to measure length to an accuracy of $0,05\text{ mm}$ (e.g. slide gauge).

4.3 Drying cabinet maintained at $(70 \pm 2)\text{ }^\circ\text{C}$.

Dimensions in millimetres

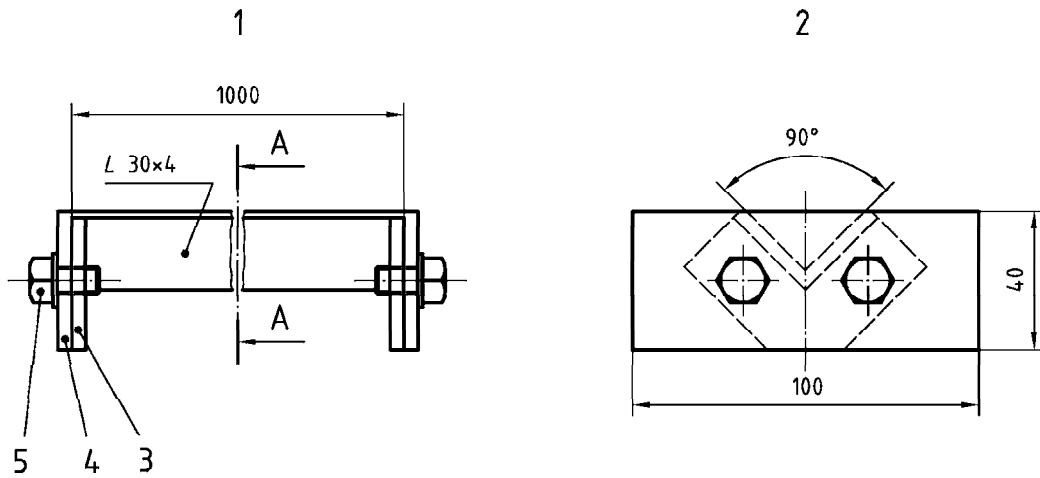


Key

- 1 Side view
- 2 Face view
- 3 Welded-on flange
- 4 Face covering
- 5 M8 x 12 – 8,8

Figure 1 — Dimensions of the trough

Dimensions in millimetres

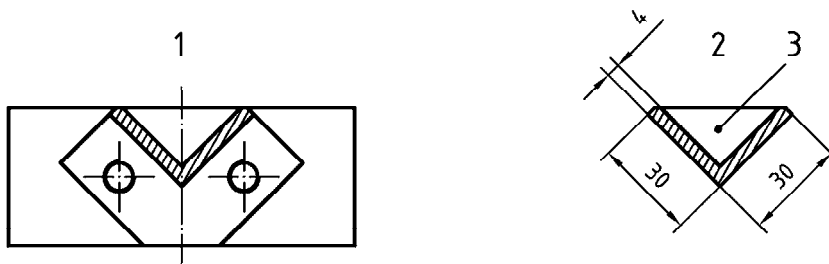

Key

- 1 Section A – A
- 2 Profile
- 3 Material under test

Figure 2 — Dimensions of the trough and position of the material under test

5 Sampling

A representative and homogenous sample of the material to be tested shall be taken in accordance with EN ISO 15528. The sample shall be examined and prepared as described in EN ISO 1513.

6 Procedure

Determine the shrinkage value using duplicate 1 000 mm troughs.

Coat the inside surfaces of the two troughs with a release agent. Mix the components of the material under test according to the manufacturer's instructions. Pour the mixture into the troughs and trowel off flush. Avoid the formation of air bubbles.

Store the two troughs in a climate of $(21 \pm 2) ^\circ\text{C}$ / $(60 \pm 10) \% \text{ r. h.}$ for 7 days. Then determine the shrinkage by aligning the cured material at one end of the trough and measuring the resulting gap at the other end of the trough within an accuracy of 0,1 mm (shrinkage value s_1).

Thereafter store the cured material, either in the trough for one day in a drying cabinet at $(70 \pm 2) ^\circ\text{C}$, followed by storage for a further day at a temperature of $(21 \pm 2) ^\circ\text{C}$. Repeat the shrinkage measurements (shrinkage value s_2).

Observe the samples for visual defects (cracks etc.).

7 Precision

Precision data are currently not available.

8 Test report

The test report shall at least include the following information:

- a) a reference to the test method standard;
- b) name and address of the test laboratory;
- c) identification number and date of the test report;
- d) name and address of the manufacturer or supplier of the product(s);
- e) name and identification marks or batch number of the product(s);
- f) date of supply of the product;
- g) date of preparation of the test specimens and any deviation from the prescribed method of preparation;
- h) conditions of storage of prepared specimens prior to test;
- i) date of test and details of the test equipment used;
- j) the test results ; single shrinkage values (s_1 and s_2) and mean shrinkage values to an accuracy of 0,1 mm/m;
- k) precision data;
- l) any deviation of this standard;
- m) date of test report and signature.

blank

BSI — British Standards Institution

BSI is the independent national body responsible for preparing British Standards. It presents the UK view on standards in Europe and at the international level. It is incorporated by Royal Charter.

Revisions

British Standards are updated by amendment or revision. Users of British Standards should make sure that they possess the latest amendments or editions.

It is the constant aim of BSI to improve the quality of our products and services. We would be grateful if anyone finding an inaccuracy or ambiguity while using this British Standard would inform the Secretary of the technical committee responsible, the identity of which can be found on the inside front cover.
Tel: +44 (0)20 8996 9000. Fax: +44 (0)20 8996 7400.

BSI offers members an individual updating service called PLUS which ensures that subscribers automatically receive the latest editions of standards.

Buying standards

Orders for all BSI, international and foreign standards publications should be addressed to Customer Services. Tel: +44 (0)20 8996 9001.
Fax: +44 (0)20 8996 7001. Email: orders@bsi-global.com. Standards are also available from the BSI website at <http://www.bsi-global.com>.

In response to orders for international standards, it is BSI policy to supply the BSI implementation of those that have been published as British Standards, unless otherwise requested.

Information on standards

BSI provides a wide range of information on national, European and international standards through its Library and its Technical Help to Exporters Service. Various BSI electronic information services are also available which give details on all its products and services. Contact the Information Centre.
Tel: +44 (0)20 8996 7111. Fax: +44 (0)20 8996 7048. Email: info@bsi-global.com.

Subscribing members of BSI are kept up to date with standards developments and receive substantial discounts on the purchase price of standards. For details of these and other benefits contact Membership Administration.
Tel: +44 (0)20 8996 7002. Fax: +44 (0)20 8996 7001.
Email: membership@bsi-global.com.

Information regarding online access to British Standards via British Standards Online can be found at <http://www.bsi-global.com/bsonline>.

Further information about BSI is available on the BSI website at <http://www.bsi-global.com>.

Copyright

Copyright subsists in all BSI publications. BSI also holds the copyright, in the UK, of the publications of the international standardization bodies. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI.

This does not preclude the free use, in the course of implementing the standard, of necessary details such as symbols, and size, type or grade designations. If these details are to be used for any other purpose than implementation then the prior written permission of BSI must be obtained.

Details and advice can be obtained from the Copyright & Licensing Manager.
Tel: +44 (0)20 8996 7070. Fax: +44 (0)20 8996 7553.
Email: copyright@bsi-global.com.